

# Modified Starch-Based Adhesives

Subjects: **Polymer Science** | **Environmental Sciences**

Contributor: Jidapa Watcharakitti , Siwaporn Smith , Ei Win ,

Consumer trends towards environmentally friendly products are driving plastics industries to investigate more benign alternatives to petroleum-based polymers. In the case of adhesives, one possibility to achieve sustainable production is to use non-toxic, low-cost starches as biodegradable raw materials for adhesive production. While native starch contains only hydroxyl groups and has limited scope, chemically modified starch shows superior water resistance properties for adhesive applications. Esterified starches, starches with ester substituents, can be feasibly produced and utilized to prepare bio-based adhesives with improved water resistance. Syntheses of esterified starch materials can involve esterification, transesterification, alkylation, acetylation, succinylation, or enzymatic reactions.

biopolymer

esterified starch

synthesis


adhesives

## 1. Introduction

Starch is one of the most abundant polysaccharides in nature, consisting of amylose and amylopectin in various ratios depending on the botanical source. Starch has been used extensively in food, medicine, and agricultural products. Due to its low cost, renewable nature and biodegradable quality, it is attracting the attention of plastic industries as a potential building block for petroleum-free adhesives, especially for paper and wood surfaces. However, the hydrophilicity of native starch makes formulating waterproof adhesives from it challenging as the starch hydroxyl groups easily form hydrogen bonds with water <sup>[1]</sup>. The introduction of hydrophobic functional groups (e.g., esters) onto native starch chains can improve its water resistance, and this can be carried out using chemical, mechanochemical, or enzymatic methods.

## 2. Esterified Starch

Esterified starch is one of the important modified starches used in the adhesive and food industries. They are typically synthesized through esterification or transesterification reactions, in which the hydroxyl groups of starch are replaced with more bulky functional groups of free fatty acids or their derivatives (**Figure 1**).

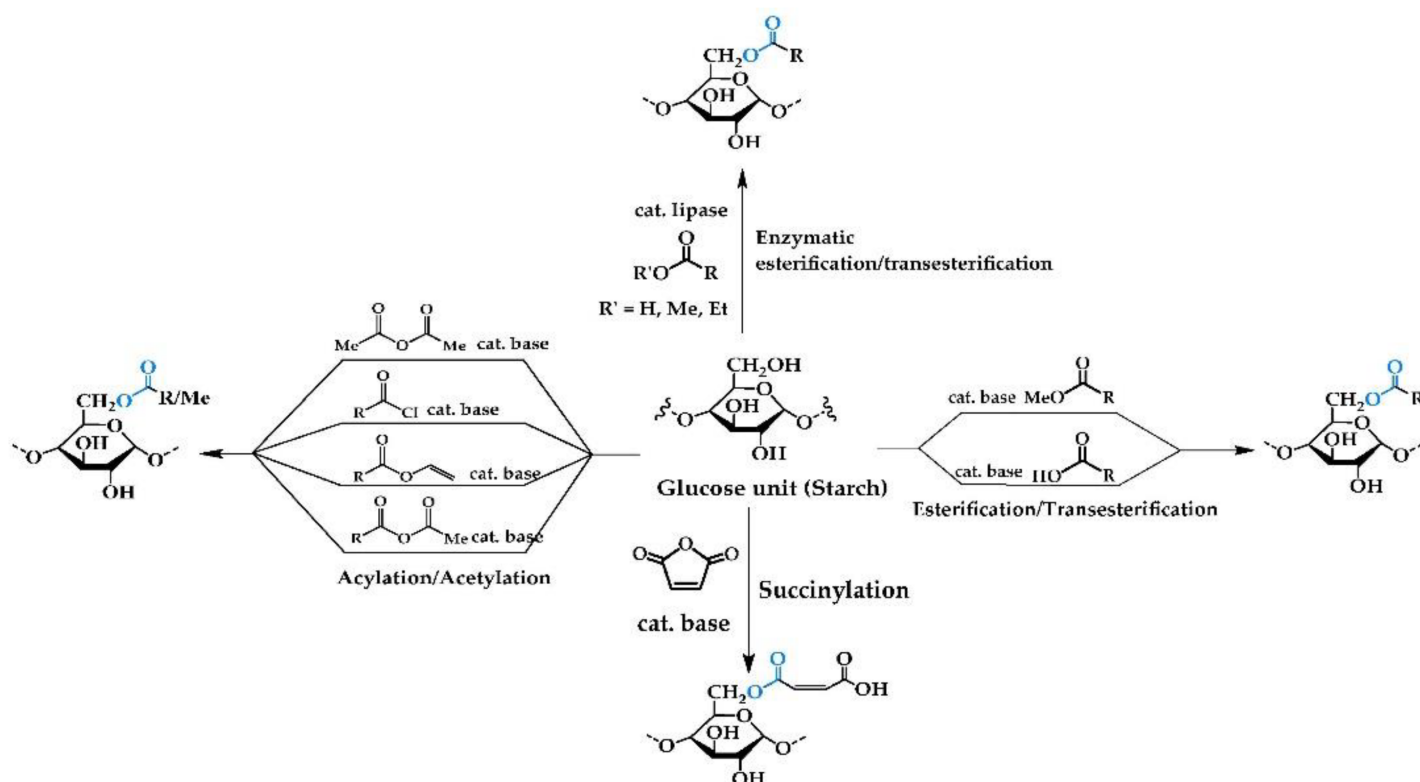

**Figure 1.** Chemical reactions for production of esterified starch.

## 2.1. Chemical Reactions

### 2.1.1. Esterification/Transesterification

Esterification is one of the most powerful chemical synthesis strategies for starch modification. These reactions typically utilize alcohols and carboxylic acids in the presence of basic catalysts such as potassium carbonate, sodium hydroxide, and sodium hydrogen phosphate [2], or acid catalysts such as *p*-toluene sulfuric acid, hydrochloric acid, and sulfuric acid. The mechanism of esterification depends on the mode of catalysis, although studies by Sakamura et al. using isotopically labelled ( $^{18}\text{O}$ ) alcohol unequivocally show that in both cases the  $^{18}\text{O}$  label is incorporated into the product at the end of the process, indicating bonding of this atom to the carbonyl carbon [3]. The mechanism of transesterification is similar but in this case involves the reaction of an alcohol with an ester, with the end result being loss of an alcohol in conjunction with formation of the esterified starch (**Figure 2**).

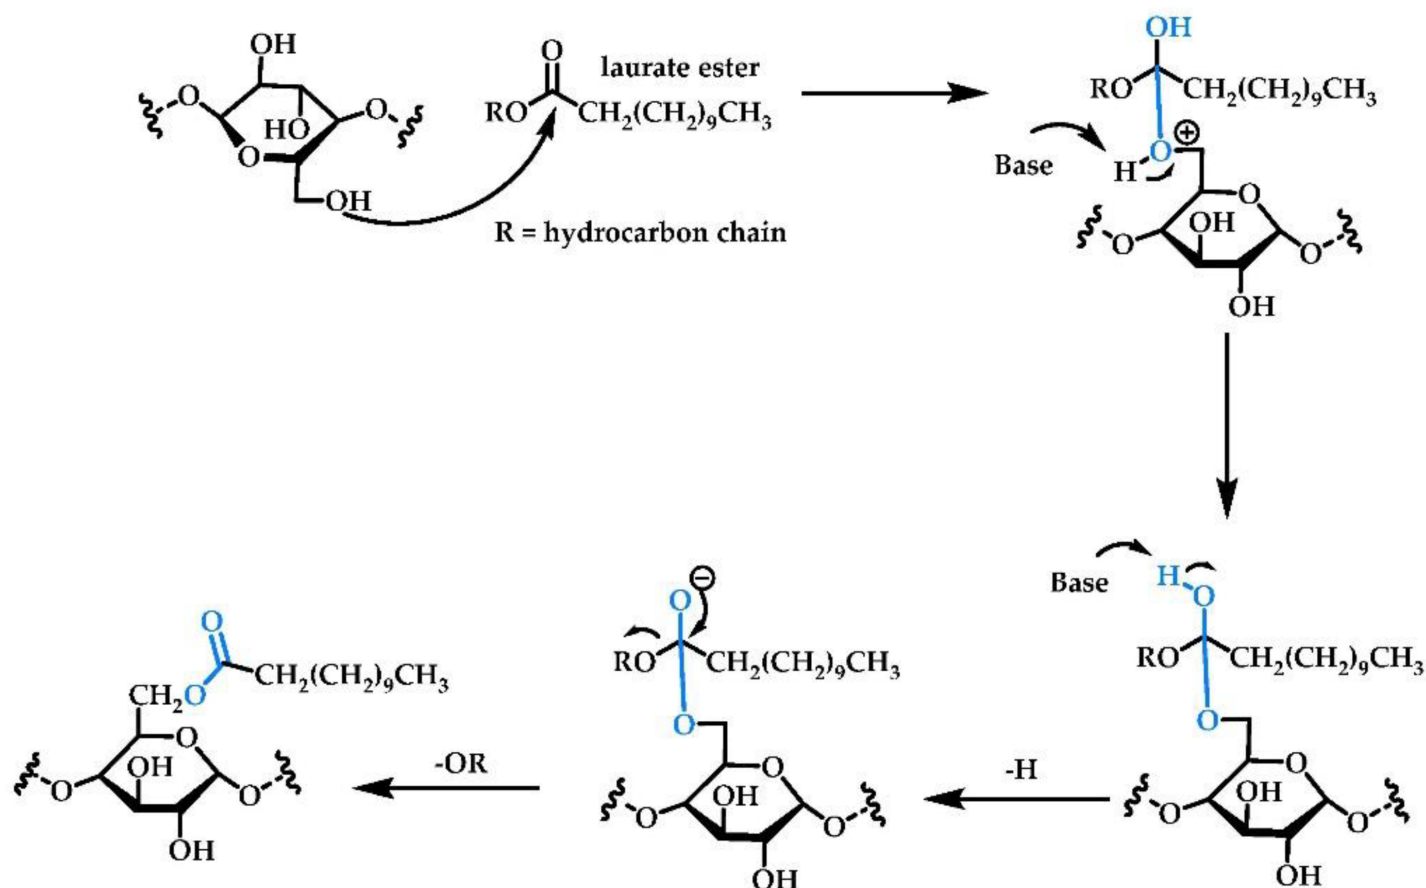


Figure 2. Transesterification of starch.

### 2.1.2. Acylation/Acetylation/Alkylation

Esterified starches can also be synthesized using acylation or acetylation reactions. In these cases, acylation involves appending the  $-\text{C(O)R}$  functional group to starch. Acetylation is a subset of acylation, which focuses only on the  $-\text{C(O)CH}_3$  group [4][5]. Compared to the previous section, acylation/acetylation involves the use of highly active acid chloride or anhydride starting materials, instead of carboxylic acids. Acid chlorides, due to their high relative reactivity [6][7], typically promote a higher degree of substitution than possible for carboxylic acids, and the  $\text{R}$  group on the acid chloride can be varied from short to long depending on application. Acid anhydrides can be employed in a similar manner [8][9]. However, these reactions have disadvantages in that these reagents are often more expensive and harder to handle than the corresponding carboxylic acids. In addition, the physicochemical properties of acetylated starch may also be affected by the acetylation reaction conditions, e.g., temperatures and pressure [10].

### 2.1.3. Succinylation

Succinylation refers to the appending of side chains to starch by the reaction with succinic anhydride. Succinic anhydride is an electrophile, which undergoes nucleophilic attack by alcohol functionalities on the starch backbone. The esterified starch product has carboxylic acid functionalities at the terminus of each chain, and this allows the product to be incorporated into the adhesive directly or be further modified or functionalized prior to use. While

succinylation results in a high degree of substitution [11][12] the limitation of this reaction is the cost of succinic anhydride. Additionally, the succinylation products have a carboxylic group at the terminal chain that could further promote cross-linking reactions between starch chains [13].

#### 2.1.4. Enzymatic Reactions with Free/Immobilized Lipase

Esterification of starch with fatty acids can be performed using enzyme catalysis, with lipases playing the key role. The use of enzymes has the advantage of not requiring extreme conditions and expensive starting materials, however the degree of substitution is often low [1][14][15] with immobilized lipase on magnetic microparticles providing a higher degree of substitution in the esterified starch than free lipase [16]. Horchani and coworkers also reported lipase immobilized calcium carbonate [17] as a catalyst in the esterification reactions between oleic acid and Maize starch. The yields of modified starch and their degree of substitution are varied, significantly depending on reaction conditions (temperature, pH, and lipase enzyme origin) [18]. Obtaining lipase from either plant or microorganisms requires multi-step isolation, purification and characterization of lipase to ensure its high purity and enzymic activity [17][19]. Additional limitations of enzymes such as low thermostability, pH sensitivity, narrow substrate scope, and low reaction yield in non-aqueous solvents [20], may result in restrictions in starch modification processes.

#### 2.1.5. Mechanochemical Processes

These processes involve reactions taking place without the addition of solvent and utilize mechanical activation, such as ball milling. In the case of starch esterification, ball milling allows for intimate mixing of starch and the esterification agent, giving good yields of product [21]. This processing also disrupts the structure and morphology of the starch, and results in changes in physicochemical properties, compared to those of native starch, such as decreased cold-water solubility, transparency, and emulsion stabilization, along with increased gelatinization temperature and viscosity [13][22][23].

### 2.2. Properties of Starches

#### 2.2.1. Degree of Substitution

The degree of substitution (DS) in esterified starch is an important factor dictating the physical properties of the material. It may be determined using  $^1\text{H-NMR}$  spectroscopy or through an acid–base titration process.

#### 2.2.2. Morphology of Native and Modified Starches

The morphology of starch granules (native and modified) can be studied using scanning electron microscopy (SEM), and this technique provides information about the granule shape, and surface features. Starch granules are the vehicle of carbohydrate storage in plant cells, and the morphology of these depends on the biochemistry of the chloroplast/amyloplasts and the physiology of the plant. Normally, native starch granules are elliptical, have a smooth surface, and range from 1 to 100  $\mu\text{m}$  in size [24]. Modification can result in the granules becoming irregular in shape with pronounced surface roughness, especially at high degrees of substitution (DS) [24][25][26].

### 2.2.3. Viscosity of Starch Pastes

In addition to the source of starch and conditions used to make the paste, functionalization of the starch can also markedly affect the viscosity of the paste. A study on the paste viscosity of OSA-esterified starch [13][27] indicated that paste obtained from this material was higher than that of native starch, as a consequence of the bulky OSA functional groups. Acylation of starch gives rise to steric interactions between starch chains, and this influences both hydrophilicity and the degree of hydrogen bonding, and thus viscosity. The viscosities of esterified starches generally decrease as the molecular weight of the ester group increases [28].

### 2.2.4. Solubility/Hydrophobicity

Appending larger functional groups onto the starch units results in increased hydrophobicity and lower water solubility. On the other hand, solubility in lower polarity solvents increases [1] and this impacts the potential application of these starch derivatives [25].

### 2.2.5. Thermal Properties of Starches


The thermal properties of starch are dependent on the amylose content or amylose/amylopectin ratio [29][30], and are also affected by functionalization. While esterified starches having low degrees of substitution (DS) do not see dramatic changes in onset temperature relative to native starch, starches having higher DS values show a decrease in gelatinization temperature [31]. Furthermore, the glass transition temperature ( $T_g$ ), the temperature at which a glassy state of amorphous materials converts into a rubbery state, is affected by structure. In the case of functionalized starch, steric hindrance between starch chains increases as the functional groups become larger, resulting in higher  $T_g$ . On the other hand, the extension of free volume of chain mobility can reduce  $T_g$  [31].

## 2.3. Adhesives Derived from Esterified Starch

Starch-based adhesives are widely used in the production of plywood [11][32] and particleboard [33][34]. Cassava starch esterified using dodecyl succinic anhydride (DDSA) as a reactant [11] and crosslinked with polymethylene polyphenyl polyisocyanate (PAPI) results in a formaldehyde-free industrial plywood adhesive with excellent viscosity, bonding strength, and water resistance properties [11]. Natural corn starch was converted to high amylose corn starch (HACS) by solvent exchange with ethanol and toluene prior to esterification with propionic anhydride in the presence of catalytic 4-dimethylaminopyridine (DMAP). The DS of these starch propionates was in the range 0.38–2.54, with higher ratios of propionic anhydride which enhanced the adhesion strength relatively to native starch. These modified starches were mixed with glycerol and polyvinyl alcohol and hot-pressed to form hot melt adhesives on Al plates. It was found that these covered a greater surface area and exhibited higher tensile strength than adhesives formed analogously from unmodified starch [35]. As mentioned in earlier sections esterified starch from chemical modifications show enhanced hydrophobicity and water resistance, with adhesives formed from this exhibiting improved bonding strength under both dry and wet conditions relative to those from natural starch [36].

## 3. Other Modified Starches for Adhesive Applications

The application of native starches in adhesives is limited due to their relatively poor shear strength, low thermal stability, and hydrophilicity [37]. Chemical modification is a successful strategy for changing the structure and properties of biopolymers to fit new applications [37] with esterification of starches discussed in the previous section being a prime example. In addition to esterification other modifications of starches can include etherification, oxidation, crosslinking, and grafted copolymerization, as shown in **Figure 3** and **Table 4**.

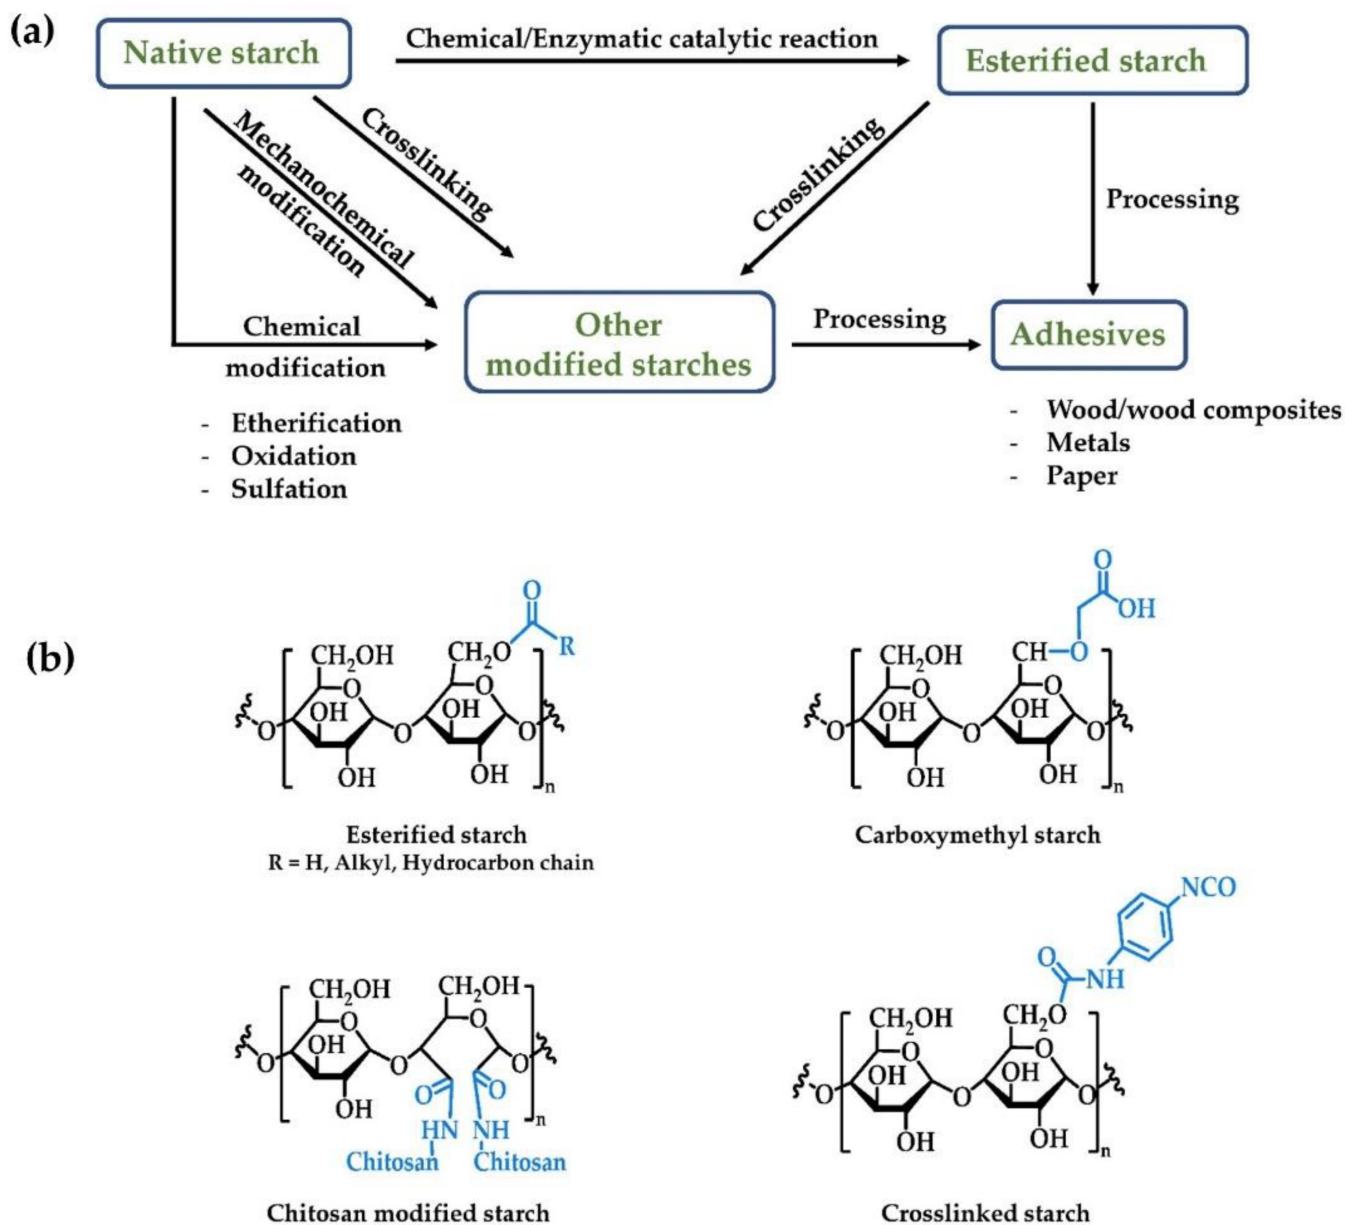

**Figure 3.** (a) Selected examples of starch modification processes being used for adhesive applications and (b) examples of the structure of modified starches. Selected examples of starch modification reactions, with given details in **Table 4**.

**Table 4.** The preparation of modified starch and adhesive application from different starch.

Reaction of Modified Starch	Starch	Properties	Utilization	Ref.	
Oxidation and modification with chitosan	Corn	Improved dry and wet shear strength of plywood	An adhesive film for plywood	[38]	ility.
Oxidation using H <sub>2</sub> O <sub>2</sub> and then crosslinking with B-pMDI and citric acid	Corn	Improved physical properties, mechanical properties, and water resistance	Medium density fiberboard	[39]	thesis of
Oxidation using KMnO <sub>4</sub> , then crosslinking and copolymerization with polyamide and methyl methacrylate	Corn	Improved wet shear strength and water resistance	An adhesive for plywood	[40]	arke
Oxidation using KMnO <sub>4</sub> , polycondensation reaction with urea and addition of nano-TiO <sub>2</sub>	Corn	The nano-TiO <sub>2</sub> effectively improves dry shear strength and viscosity of the nano-TiO <sub>2</sub> -U-OST adhesive.	An adhesive	[41]	xygen OC.
Oxidation using H <sub>2</sub> O <sub>2</sub> and crosslinking with polyamidoamine-epichlorohydrin (PAH)	Rice	Enhanced thermal stability, hydrophobicity, wet-cohesion, and adhesiveness	An adhesive for wood composites	[42]	1. ynthesis
Etherification with carboxymethyl and use of POCl <sub>3</sub> as crosslinking agent	Wheat	The modified starch mixed with PVA improves solid content, heat and water resistance but decrease viscosity.	Adhesive for particleboard	[34]	erties of 721.
Etherification with epichlorohydrin	Oil palm	Improved mechanical strength (modulus, elasticity, and internal bond), solid content and viscosity	Adhesive for particleboard	[43]	ayiotou rch. J.
Graft copolymerization with glycidyl methacrylate (GMA) and crosslinking with sodium trimetaphosphate (STMP).	Cassava	Improved water resistance and bonding strength	An adhesive for plywood	[44]	modified 0300. ed
Graft copolymerization with sodium dodecyl sulfate (SDS)	Micronized (MS)	Improved shear strength and decreased viscosity of micronized starch with increasing SDS contents	Wood adhesive	[45]	prepared
Graft copolymerization with lignin	Corn	Improved adhesive bond strength and moisture resistance, including extended shelf-life.	An adhesive for paper	[46]	3 cromol.
Crosslinking with polyphenylene isocyanate (PAPI) with poly vinyl alcohol (PVOH) as a protective colloid	Cassava	Improved water resistance, shear strength, mobility and storage stability of starch adhesive	Wood adhesive	[47]	24, 60–

13. Hu, H.; Liu, W.; Shi, J.; Huang, Z.; Zhang, Y.; Huang, A.; Yang, M.; Qin, X.; Shen, F. Structure and functional properties of octenyl succinic anhydride modified starch prepared by a non-conventional technology. *Starch-Starke* 2016, 68, 151–159.



1	Reaction of Modified Starch	Starch	Properties	Utilization	Ref.	starch.
1	Crosslinking with lignin	Corn	Lignin improved the strength and water resistance of adhesive	An adhesive for cardboard application	[48]	ate in

Ionic Liquids. J. Agric. Food Chem. 2013, 61, 9882–9891.

Etherification can be used to modify the water resistance properties of starch through the introduction of lipophilic functional groups. This is generally accomplished by treating starch with epoxides, such as propylene or ethylene esters by immobilized lipase on magnetic microparticles. Biosci. Biotechnol. BioChem. 2015, 79, 1750–1758.

17. Hordani, H.; Chabouni, M.; Gargouri, T.; Sayala, A. Solvent-free lipase catalyzed synthesis of long chain starch esters using starches in adhesives. Crosslinked starch exhibits superior mechanical (tensile strength), thermal, and water stability compared to native starch. [49][50][51]. Carbohydr. Polym. 2016, 79, 466–474.

18. Luna, C.; Luna, D.; Calero, J.; Bautista, F.M.; Romero, A.A.; Posadillo, A.; Verdugo-Escamilla, C. 7—Biochemical catalytic production of biodiesel. In Handbook of Biofuels Production, 2nd ed.; Woodhead Publishing: Sawston, UK, 2016; pp. 165–199.

19. Hesham, O.; Aderkun, A.E.; Omosaye, S.A.; Olorode, E.M.; Ogundiran, A.E. Isolation, characterization, and molecular characterization of lipase producing bacteria from contaminated soil. Sci. Afr. 2020, 8, e00279.

The unique properties of nanoparticles such as their small size, high surface energy, and the ability to functionalize their surfaces render them attractive for the development of high-performance composite materials. Nano-TiO<sub>2</sub>, nano-SiO<sub>2</sub>, and montmorillonite (MMT) nanoparticles have been used as crosslinking or grafting agents to improve the characteristics of biopolymer-based adhesives in recent years [53][54]. Significant improvements in water resistance and bonding strength were found when nano-TiO<sub>2</sub> [41][55], Selge coupling agent [53], acrylate [32][56], and polyvinylamine [42][57] were used as crosslinking or grafting agents with the starch for adhesive purposes. Assisted by Mechanical Activation with Stirring Ball Mill as Reactor. Ind. Eng. Chem. Res. 2014, 53, 2114–2120.

Natural polymers derived from biomass (lignin, cellulose, hemicellulose), and chitosan have the potential to be used as bridging agents in adhesive formulations. These may be useful in systems containing inorganic materials and organic components such as starch, and their use can improve the adhesive properties of the formulation [42][46]. Blending starch with hydrophobic biopolymers (such as lignin) could be a strategy for improving the water-resistance of the adhesive and altering its mechanical properties.

23. Huang, Z.Q.; Lu, J.P.; Li, X.H.; Tong, Z.H. Effect of mechanical activation on physicochemical properties and structure of cassava starch. Carbohydr. Polym. 2007, 68, 128–135.

24. Wang, S.Y.; Zhang, C.; Liu, Q.Q.; Wang, Z.J.; Wan, K.X.; Qian, J.Y.; Zhang, L.; Wu, C.; Li, Q. Modification of potato starch by critical melting pretreatment combined with freeze-thawing: Preparation, morphology, structure, and functionality. LWT 2022, 158, 113109.

25. Ojogbo, E.; Blanchard, R.; Mekonnen, T. Hydrophobic and Melt Processable Starch-Laurate Esters: Synthesis, Structure–Property Correlations. J. Polym. Sci. Part A Polym. Chem. 2018, 56, 2611–2622.



26. Wang, Z.; Zhu, H.; Huang, J.; Ge, Z.; Guo, J.; Feng, X.; Xu, Q. Improvement of the bonding properties of cassava starch-based wood adhesives by using different types of acrylic ester. *Int. J. Biol. Macromol.* 2019, 126, 603–611.
27. Hui, R.; Qi-he, C.; Liang, F.M.; Qiong, X.; Guo-qing, H. Preparation and properties of octenyl succinic anhydride modified potato starch. *Food Chem.* 2009, 114, 81–86.
28. Muljana, H.; Knoop, S.V.D.; Keijzer, D.; Picchioni, F.; Janssen, L.P.B.M.; Heeres, H.J. Synthesis of fatty acid starch esters in supercritical carbon dioxide. *Carbohydr. Polym.* 2010, 82, 346–354.
29. Zhu, J.; Zhang, S.; Zhang, B.; Qiao, D.; Pu, H.; Liu, S.; Li, L. Structural features, and thermal property of propionylated starches with different amylose/amylopectin ratio. *Int. J. Biol. Macromol.* 2017, 97, 123–130.
30. Vamadevan, V.; Bertoft, E.; Seetharaman, K. On the importance of organization of glucan chains on thermal properties of starch. *Carbohydr. Polym.* 2013, 92, 1653–1659.
31. Silaket, P.; Chatakanonda, P.; Tran, T.; Wansuksri, R.; Piyachomkwan, K.; Sriroth, K. Thermal properties of esterified cassava starches and their maltodextrins in various water systems. *Starch-Starke* 2014, 66, 1022–1032.
32. Xu, Q.; Wen, J.; Wang, Z. Preparation and Properties of Cassava Starch-based Wood Adhesives. *BioResources* 2016, 11, 6756–6767.
33. Owodunni, A.A.; Lamaming, J.; Hashim, R.; Abdulwahab Taiwo, O.F.; Hussin, M.H.; Mohamad Kassim, M.H.; Bustami, Y.; Sulaiman, O.; Mohamad Amini, M.H.; Hiziroglu, S. Properties of green particleboard manufactured from coconut fiber using a potato starch-based adhesive. *BioResources* 2020, 15, 2279–2292.
34. Lamaming, J.; Heng, N.B.; Owodunni, A.A.; Lamaming, S.Z.; Khadir, N.K.A.; Hashim, R.; Sulaiman, O.; Kassim, M.H.M.; Hussin, M.H.; Bustami, Y.; et al. Characterization of rubberwood particleboard made using carboxymethyl starch mixed with polyvinyl alcohol as adhesive. *Compos. Part B Eng.* 2020, 183, 107731.
35. Zhang, Z.; Macquarrie, D.; Clark, J.H.; Matharu, A.S. Chemical modification of starch and the application of expanded starch and its esters in hot melt adhesive. *RSC Adv.* 2014, 4, 41947–41955.
36. Wang, Z.; Li, Z.; Gu, Z.; Hong, Y.; Cheng, L. Preparation, characterization, and properties of starch-based wood adhesive. *Carbohydr. Polym.* 2012, 88, 699–706.
37. Huicochea, E.F. Introductory Chapter: Starch Modifications. *Applications of Modified Starches*; Huicochea, E.F., Villalobos, R.R., Eds.; InTechOpen: London, UK, 2018; p. 78.
38. Li, D.; Zhuang, B.; Wang, X.; Wu, Z.; Wei, W.; Aladejana, J.Y.; Hou, X.; Yves, K.G.; Xie, Y.; Liu, J. Chitosan used as a specific coupling agent to modify starch in preparation of adhesive film. *J.*

- Clean. Prod. 2020, 277, 123210.
39. Lubis, M.A.R.; Park, B.D.; Hong, M.K. Tuning of Adhesion and Disintegration of Oxidized Starch Adhesives for the Recycling of Medium Density Fiberboard. *BioResources* 2020, 15, 5156–5178.
  40. Su, M.; Wu, J.; Pan, P.; Wang, H. Preparation, and characterization of a water-resistant polyamide-oxidized starch-methyl methacrylate eco-friendly wood adhesive. *Int. J. Biol. Macromol.* 2022, 194, 763–769.
  41. Zhao, X.F.; Peng, L.Q.; Wang, H.L.; Wang, Y.B.; Zhang, H. Environment-friendly urea-oxidized starch adhesive with zero formaldehyde-emission. *Carbohydr. Polym.* 2018, 181, 1112–1118.
  42. Yin, H.; Zheng, P.; Zhang, E.; Rao, J.; Lin, Q.; Fan, M.; Zhu, Z.; Zeng, Q.; Chen, N. Improved wet shear strength in eco-friendly starch-cellulosic adhesives for woody composites. *Carbohydr. Polym.* 2020, 250, 116884.
  43. Sulaiman, N.S.; Hahim, R.; Amini, M.H.M.; Sulaiman, O.; Hiziroglu, S. Evaluation of the Properties of Particleboard Made Using Oil Palm Starch Modified with Epichlorohydrin. *BioResources* 2013, 8, 283–301.
  44. Chen, X.; Sun, C.; Wang, Q.; Tan, H.; Zhang, Y. Preparation of glycidyl methacrylate grafted starch adhesive to apply in high-performance and environment-friendly plywood. *Int. J. Biol. Macromol.* 2022, 194, 954–961.
  45. Chen, L.; Xiong, Z.; Li, Q.; Din, Z.U.; Xiong, H. Sodium dodecyl sulfate improves the properties of bio-based wood adhesive derived from micronized starch: Microstructure and rheological behaviors. *Int. J. Biol. Macromol.* 2019, 140, 1026–1036.
  46. Wu, Q.; Shao, W.; Xia, N.; Wang, P.; Kong, F. A separable paper adhesive based on the starch—lignin composite. *Carbohydr. Polym.* 2020, 229, 115488.
  47. Jiang, Y.; Chen, Q.; Tan, H.; Gu, J.; Zhang, Y. A Low-Cost, Formaldehyde-Free, and High-Performance Starch-based Wood Adhesive. *BioResources* 2019, 14, 1405–1418.
  48. Nasiri, A.; Wearing, J.; Dubé, M.A. Using Lignin to Modify Starch-Based Adhesive Performance. *ChemEngineering* 2020, 4, 3.
  49. Detduangchan, N.; Sridach, W.; Wittaya, T. Enhancement of the properties of biodegradable rice starch films by using chemical crosslinking agents. *Int. Food Res. J.* 2014, 21, 1189–1199.
  50. Kim, M.; Lee, S.J. Characteristics of crosslinked potato starch and starch-filled linear low-density polyethylene films. *Carbohydr. Polym.* 2002, 50, 331–337.
  51. Seligra, P.G.; Jaramillo, C.M.; Fama, L.; Goyanes, S. Biodegradable and non-retrogradable eco-films based on starch—glycerol with citric acid as crosslinking agent. *Carbohydr. Polym.* 2016, 138, 66–74.

52. Praveen, T.K.; Bhushanam, M.V.N.; Prasad, Y.R. Preparation, Evaluation and Characterization of Starch and Grafted Starch. *IJPSR* 2021, 12, 4001–4010.
53. Zhang, Y.; Ding, L.; Gu, J.; Tan, H.; Zhu, L. Preparation, and properties of a starch-based wood adhesive with high bonding strength and water resistance. *Carbohydr. Polym.* 2015, 115, 32–37.
54. Li, Z.; Wang, J.; Li, C.; Gu, Z.; Cheng, L.; Hong, Y. Effects of montmorillonite addition on the performance of starch-based wood adhesive. *Carbohydr. Polym.* 2015, 115, 394–400.
55. Chen, L.; Xiong, Z.; Xiong, H.; Wang, Z.; Din, Z.U.; Nawaz, A.; Wang, P.; Hu, C. Effects of nano-TiO<sub>2</sub> on bonding performance, structure stability and film-forming properties of starch-g-VAc based wood adhesive. *Carbohydr. Polym.* 2018, 200, 477–486.
56. Zia-ud-Din; Chen, L.; Ullah, I.; Wang, P.K.; Javaid, A.B.; Hu, C.; Zhang, M.; Ahamd, I.; Xiong, H.; Wang, Z. Synthesis, and characterization of starch-g-poly (vinyl acetate-co-butyl acrylate) bio-based adhesive for wood application. *Int. J. Biol. Macromol.* 2018, 114, 1186–1193.
57. Zhang, Y.; Chen, M.; Zhang, J.; Li, J.; Shi, S.Q.; Gao, Q. A High-Performance Bio-Adhesive Using Hyperbranched Aminated Soybean Polysaccharide and Bio-Based Epoxide. *Adv. Mater. Interfaces* 2020, 7, 2000148.

---

Retrieved from <https://encyclopedia.pub/entry/history/show/56674>