

# Metal Halide Perovskites as Photocatalysts

Subjects: Chemistry, Applied

Submitted by:  Lorenzo

Malavasi

## Definition


The possible use of MHPs as effective photocatalysts has become clear to the scientific community in the last few years. Bulk and nanocrystalline metal halide perovskites have been shown to be excellent semiconductors with suitable energy levels to run most of the key solar-driven reactions of current interest for solar fuels production. This review summarized the current status of the application of MHPs in photocatalyzed organic syntheses/transformation which to date have shown, in most of the cases, significant advantages with respect to traditional photocatalysts.

---

## 1. Introduction

In nature, solar light is absorbed as storable energy in chemical bonds through a vast array of biochemical reactions (C-C, C-O, and C-N forming reactions) during the photosynthetic process. Based on this consideration, using light to induce chemical reactions (photochemistry) is an attractive strategy involving photons as traceless and sustainable reagents to provide energy for the activation of substrates and reagents. Traditionally, photochemical reactions were performed using UV light to excite substrates. However, this approach requires high energy that can be provided by special and expensive equipment leading to unselective reactions, which are difficult to control and predict. By the development of photocatalysts activated with low-energy photons, many advances have been made in this field, leading to sustainable chemical transformation driven by visible light. Photocatalysts can induce chemical reactions through several mechanistic pathways, namely photoredox catalysis, proton-coupled electron transfer, hydrogen atom transfer, and energy transfer. These mechanisms are summarized and briefly explained in **Figure 1** [1]. By the way, the photocatalytic approach for the construction of valuable chemicals is a promising technique to reach a cost-effective and efficient methodology in organic chemistry [2][3]. However, many drawbacks are related to the most common catalysts currently used, such as the expensive metals required, the need of anaerobic reaction conditions, low or moderate reaction yields, and complicated preparation protocols [3][4][5][6][7][8]. Therefore, the main challenge for the development of photocatalytic procedures in organic chemistry is to achieve easy-to-produce, low-cost, and efficient catalysts to be used in several chemical bond-forming reactions. Due to the extremely appealing photophysical properties showed by metal halide perovskites (MHPs) and exploited in photovoltaics [9], these materials represent an attractive strategy to produce valuable photocatalysts [10][11]. According to the current literature, these excellent photovoltaic performances can be attributed to the unique optoelectronic properties of MHPs [12] such as strong light absorption [13], good charge-carrier lifetimes [14], and high diffusion lengths [15]. Therefore, the investigation of perovskite photocatalytic properties for organic synthesis was inspired by their superior optical properties [16][17][18][19]. Moreover, MHPs can also be produced in a very cost-effective manner, leading to the obtainment of versatile materials, prepared from earth-abundant and cheap starting elements [20]. Indeed, perovskites-based materials are very promising candidates as photocatalysts for organic reactions under visible light for the formation of, among others, C-C, C-N, and C-O bonds [2]. The superior optical properties of MHPs make them suitable to promote several catalytic reactions such as reduction and oxidation processes, thanks to their electronic structure, their highly tunable and narrow band gap, long carrier lifetimes and good defect tolerance. The mechanisms involved in these photocatalytic reactions using MHPs are similar to those of conventional catalysts: the visible-light generation of charge carriers occurs and then they are transferred to the reaction sites, often through the mediation of a metal or a semiconductor cocatalyst [21]. The possibility of developing low-cost, easy-to-produce, highly efficient, and tunable MHPs-based photocatalysts may bring new and promising tools in chemical synthesis and organic reactions. For these reasons, in the present review, we report the current status regarding the application of MHPs

photocatalysts in organic reactions, by considering the application of lead-containing and lead-free materials. For the first class, we further organized the review by summarizing the available results on bulk and nanocrystalline MHPs separately, due to the peculiar properties induced by grain size reduction on the optical characteristics and in turn on the photocatalytic activity [20][22][23].

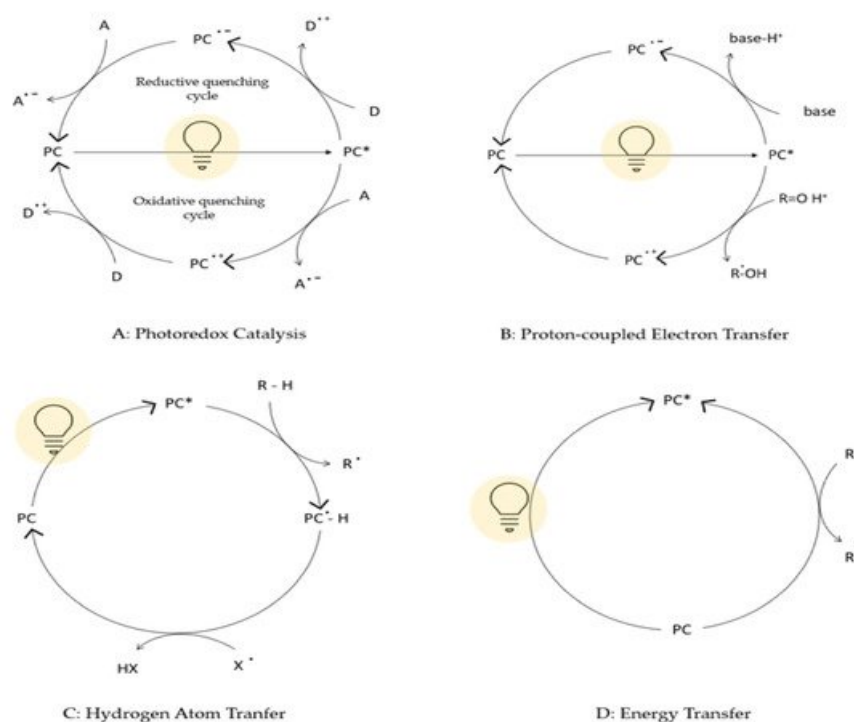

**Figure 1.** General mechanistic scenarios in photocatalytic synthesis. In all the pathways reported, the first step concerns the formation of an excited photocatalyst upon irradiation ( $PC^*$ ). **(A)** Photoredox Catalysis:  $PC^*$  accepts or donates a single electron leading to oxidative or reductive quenching cycles depending on the substrates present in the reaction mixture (presence of electron acceptor or donor); **(B)** Proton-coupled Electron Transfer: redox events occur during a concerted proton transfer; **(C)** Hydrogen Atom Transfer: homolytic cleavage of C-H bonds by the photocatalyst or after singlet electron transfer events; **(D)** Energy Transfer: PC directly transfers its excited state energy to a substrate that normally is not able to absorb light (at the given wavelength) leading to a chemical reaction. Reprinted with permission from ref. [1]. Copyright 2021 iScience.

## 2. Lead-Based MHPs

Wang et al. also performed an  $\alpha$ -alkylation reaction of aldehydes using  $CsPbBr_3$  NCs as photocatalyst [24]. In this work, an amine-free method was employed for the colloidal NCs synthesis to avoid unwanted charge transfer (CT) to the aminic ligand.

In addition, the possibility of creating MHP-based photocatalytic composites may bring new tools in organic synthesis, thanks to the great tunability in the band gap of MHPs allowing to modify the relative band-alignment between two semiconductors, thus taking advantage of the relative efficiencies [21].

Li et al. studied as well the photocatalysis of the polymerization of TerEDOT by employing Br/I alloyed  $CsPbX_3$  ( $X = I, I 0.67 Br 0.33, I 0.5 Br 0.5, I 0.33 Br 0.67, Br$ ) [25]. All the NCs show a cubic morphology, with an average size of 10.6 nm. The authors verified that the catalytic activity increases with the iodine content, correlating this feature to the band gap narrowing and the exciton binding energy decrease [25]. For the NCs synthesis, the classical hot-injection method, using both amine and carboxylic ligands (OA and oleyl amine (OLA)), was performed. They also tried to replace OA with acetic acid, via treatment with methyl acetate (MeAc), obtaining an enhanced photocatalytic activity, which has been attributed to an improved CT [25].

Corti et al. highlight that this is the first application of metal halide perovskites-based composites for the

generation of singlet oxygen, leading to the development of a platform to further expand the knowledge and applicability of this class of catalyst for photochemical reactions [26].

### 3. Lead-Free MHPs

There are few examples of the application of lead-free MHPs in photocatalysis, like the ones listed in **Table 1**, possibly due to some stability limitation of tin (the preferred substituent for Pb) and, in general, for the fact that expansion of lead-free materials to other fields in addition to photovoltaics is still in its infancy.

**Table 1.** Pb-free photocatalytic systems reviewed in the present paper highlighting the reaction, reaction yield, and illumination mean.

Catalyst		Reaction	Reaction Yield	Illumination	Reference
HDA <sub>2</sub> SnI <sub>4</sub> (HAD = hexadecylammonium)		Decarboxylation of indoline-2-carboxylic acid	30%	White LED	[27]
		Dehydrogenation of indoline-2-carboxylic acid	47%		
Cs <sub>3</sub> Bi <sub>2</sub> Br <sub>9</sub>		ring-opening of epoxides	Up to 88%	λ > 420 nm	[28]
Cs <sub>3</sub> Bi <sub>2</sub> Br <sub>9</sub>		Toluene oxidation	0.23%	Xe lamp (λ > 420 nm)	[29]
Cs <sub>3</sub> Sb <sub>2</sub> Br <sub>9</sub>		Toluene oxidation	-	λ > 420 nm	[30]
PEA <sub>2</sub> SnBr <sub>4</sub>	Supported onto C <sub>3</sub> N <sub>4</sub>	<sup>1</sup> O <sub>2</sub> hetero Diels-Alder cycloaddition reaction	26%	Simulated solar light	[26]
DMASnBr <sub>3</sub>	Supported onto C <sub>3</sub> N <sub>4</sub>		63%		

HDA 2SnI 4 (HAD = hexadecylammonium) has been proposed by Hong et al. for photocatalytic decarboxylation and dehydrogenation reactions, exactly as in the previous section with HDA 2PbI 4 (see “bulk” section, Hong et al.) [27].

The same compounds have been employed by Dai et al. for the photocatalysis of the selective benzylic C-H bond activation [29]. The authors exploited mesoporous silica-supported Cs 3Bi 2Br 9 nanoparticles, with sizes 2–5 nm, and loadings from 5–40% weight. They studied toluene oxidation as a model reaction and managed to obtain good conversion rates and 90% selectivity towards benzaldehyde production with the 10% perovskite sample [29]. The group also determined that the reaction proceeds via a radical mechanism ( **Figure 6** b,c) in which toluene interacts with the excited perovskite to produce a carbon radical, reacts with atmospheric oxygen to form benzylic acid, which lastly decomposes to form benzaldehyde and water [29].

Finally, Corti et al. studied the coupling of a lead-free 2D/3D metal halide perovskite with g-C 3N 4 to create novel catalytic systems for sustainable singlet oxygen generation, namely, g-C 3N 4/PEA 2SnBr 4 and g-C 3N 4/DMASnBr 3 [26].

### 4. Conclusions

The possible use of MHPs as effective photocatalysts has become clear to the scientific community in the last few years. Bulk and nanocrystalline metal halide perovskites have been shown to be excellent semiconductors with suitable energy levels to run most of the key solar-driven reactions of current interest for solar fuels production [2]. This review summarized the current status of the application of MHPs in photocatalyzed organic syntheses/transformation which to date have shown, in most of the cases, significant advantages with respect to traditional photocatalysts. It is clear that the use of MHPs in

this field is still in infancy and that more extended work, to widen the library of organic reactions where they can be advantageously applied, is still required. At the same time, rigorous mechanistic studies will reveal the advantages as well limitations of their use with respect to common catalytic systems. However, MHPs possess a unique capability of chemical structure and electronic properties tunability which will for sure allow finding optimal photocatalysts for most of the expected applications. The promising results reported so far allow us to predict a further growth of the branch in different directions: the testing of syntheses not reported yet by means of already known halide perovskite photocatalysts, the use of new phases with a significant focus on lead-free materials, and the exploitation of effective heterostructures to further improve the catalytic activity.

## References

1. Reischauer, S.; Pieber, B. Emerging Concepts in Photocatalytic Organic Synthesis. *iScience* 2021, 24, 102209.
2. Zhu, X.; Lin, Y.; San Martin, J.; Sun, Y.; Zhu, D.; Yan, Y. Lead Halide Perovskites for Photocatalytic Organic Synthesis. *Nat. Commun.* 2019, 10, 2843.
3. Romero, N.A.; Nicewicz, D.A. Organic Photoredox Catalysis. *Chem. Rev.* 2016, 116, 10075–10166.
4. Prier, C.K.; Rankic, D.A.; MacMillan, D.W. Visible Light Photoredox Catalysis with Transition Metal Complexes: Applications in Organic Synthesis. *Chem. Rev.* 2013, 113, 5322–5363.
5. Li, X.; Li, Z.; Gao, Y.; Meng, Q.; Yu, S.; Weiss, R.G.; Tung, C.; Wu, L. Mechanistic Insights into the Interface-directed Transformation of Thiols into Disulfides and Molecular Hydrogen by Visible-light Irradiation of Quantum Dots. *Angew. Chem.* 2014, 126, 2117–2121.
6. Zhang, Z.; Edme, K.; Lian, S.; Weiss, E.A. Enhancing the Rate of Quantum-Dot-Photocatalyzed Carbon–Carbon Coupling by Tuning the Composition of the Dot’s Ligand Shell. *J. Am. Chem. Soc.* 2017, 139, 4246–4249.
7. Cherevatskaya, M.; Neumann, M.; Földner, S.; Harlander, C.; Kümmel, S.; Dankesreiter, S.; Pfitzner, A.; Zeitler, K.; König, B. Visible-light-promoted Stereoselective Alkylation by Combining Heterogeneous Photocatalysis with Organocatalysis. *Angew. Chem. Int. Ed.* 2012, 51, 4062–4066.
8. Nicewicz, D.A.; MacMillan, D.W. Merging Photoredox Catalysis with Organocatalysis: The Direct Asymmetric Alkylation of Aldehydes. *Science* 2008, 322, 77–80.
9. Burschka, J.; Pellet, N.; Moon, S.-J.; Humphry-Baker, R.; Gao, P.; Nazeeruddin, M.K.; Grätzel, M. Sequential Deposition as a Route to High-Performance Perovskite-Sensitized Solar Cells. *Nature* 2013, 499, 316–319.
10. Saparov, B.; Mitzi, D.B. Organic-Inorganic Perovskites: Structural Versatility for Functional Materials Design. *Chem. Rev.* 2016, 116, 4558–4596.
11. Zhu, X.; Lin, Y.; Sun, Y.; Beard, M.C.; Yan, Y. Lead-Halide Perovskites for Photocatalytic  $\alpha$ -Alkylation of Aldehydes. *J. Am. Chem. Soc.* 2019, 141, 733–738.
12. Mao, L.; Stoumpos, C.C.; Kanatzidis, M.G. Two-Dimensional Hybrid Halide Perovskites: Principles and Promises. *J. Am. Chem. Soc.* 2018, 141, 1171–1190.
13. Yang, Y.; Yang, M.; Moore, D.T.; Yan, Y.; Miller, E.M.; Zhu, K.; Beard, M.C. Top and Bottom Surfaces Limit Carrier Lifetime in Lead Iodide Perovskite Films. *Nat. Energy* 2017, 2, 16207.
14. Yang, Y.; Ostrowski, D.P.; France, R.M.; Zhu, K.; Van De Lagemaat, J.; Luther, J.M.; Beard, M.C. Observation of a Hot-Phonon Bottleneck in Lead-Iodide Perovskites. *Nat. Photonics* 2016, 10, 53–59.
15. Dong, Q.; Fang, Y.; Shao, Y.; Mulligan, P.; Qiu, J.; Cao, L.; Huang, J. Electron-Hole Diffusion Lengths > 175 nm in Solution-Grown CH<sub>3</sub>NH<sub>3</sub>PbI<sub>3</sub> Single Crystals. *Science* 2015, 347, 967–970.
16. Xu, Y.-F.; Yang, M.-Z.; Chen, B.-X.; Wang, X.-D.; Chen, H.-Y.; Kuang, D.-B.; Su, C.-Y. A CsPbBr<sub>3</sub> Perovskite Quantum Dot/Graphene Oxide Composite for Photocatalytic CO<sub>2</sub> Reduction. *J. Am. Chem. Soc.* 2017, 139, 5660–5663.
17. Chen, K.; Deng, X.; Dodekatos, G.; Tüysüz, H. Photocatalytic Polymerization of 3,4-Ethylenedioxythiophene over Cesium Lead Iodide Perovskite Quantum Dots. *J. Am. Chem. Soc.* 2017, 139, 12267–12273.
18. Wong, Y.; De Andrew Ng, J.; Tan, Z. Perovskite-initiated Photopolymerization for Singly Dispersed Luminescent Nanocomposites. *Adv. Mater.* 2018, 30, 1800774.
19. Wu, W.-B.; Wong, Y.-C.; Tan, Z.-K.; Wu, J. Photo-Induced Thiol Coupling and C–H Activation Using Nanocrystalline Lead-Halide Perovskite Catalysts. *Catal. Sci. Technol.* 2018, 8, 4257–4263.
20. Zhao, Y.; Zhu, K. Organic-Inorganic Hybrid Lead Halide Perovskites for Optoelectronic and Electronic Applications. *Chem. Soc. Rev.* 2016, 45, 655–689.
21. Romani, L.; Malavasi, L. Solar-Driven Hydrogen Generation by Metal Halide Perovskites: Materials, Approaches, and Mechanistic View. *ACS Omega* 2020, 5, 25511–25519.
22. Feng, A.; Jiang, X.; Zhang, X.; Zheng, X.; Zheng, W.; Mohammed, O.F.; Chen, Z.; Bakr, O.M. Shape Control of Metal Halide Perovskite Single Crystals: From Bulk to Nanoscale. *Chem. Mater.* 2020, 32, 7602–7617.
23. González-Carrero, S.; Galian, R.E.; Pérez-Prieto, J. Organometal Halide Perovskites: Bulk Low-Dimension Materials and

- Nanoparticles. Part. Part. Syst. Charact. 2015, 32, 709–720.
24. Wang, K.; Lu, H.; Zhu, X.; Lin, Y.; Beard, M.C.; Yan, Y.; Chen, X. Ultrafast Reaction Mechanisms in Perovskite Based Photocatalytic C–C Coupling. *ACS Energy Lett.* 2020, 5, 566–571.
  25. Li, Y.; Shu, Q.; Du, Q.; Dai, Y.; Zhao, S.; Zhang, J.; Li, L.; Chen, K. Surface Modification for Improving the Photocatalytic Polymerization of 3,4-Ethylenedioxythiophene over Inorganic Lead Halide Perovskite Quantum Dots. *ACS Appl. Mater. Interfaces* 2020, 12, 451–460.
  26. Corti, M.; Chiara, R.; Romani, L.; Mannucci, B.; Malavasi, L.; Quadrelli, P. G-C3N4/Metal Halide Perovskite Composites as Photocatalysts for Singlet Oxygen Generation Processes for the Preparation of Various Oxidized Synthons. *Catal. Sci. Technol.* 2021, 11, 2292–2298.
  27. Hong, Z.; Chong, W.K.; Ng, A.Y.R.; Li, M.; Ganguly, R.; Sum, T.C.; Soo, H.S. Hydrophobic Metal Halide Perovskites for Visible-Light Photoredox C–C Bond Cleavage and Dehydrogenation Catalysis. *Angew. Chem. Int. Ed.* 2019, 58, 3456–3460.
  28. Dai, Y.; Tüysüz, H. Lead-Free Cs<sub>3</sub>Bi<sub>2</sub>Br<sub>9</sub> Perovskite as Photocatalyst for Ring-Opening Reactions of Epoxides. *ChemSusChem* 2019, 12, 2587–2592.
  29. Dai, Y.; Poidevin, C.; Ochoa-Hernández, C.; Auer, A.A.; Tüysüz, H. A Supported Bismuth Halide Perovskite Photocatalyst for Selective Aliphatic and Aromatic C–H Bond Activation. *Angew. Chem. Int. Ed.* 2020, 59, 5788–5796.
  30. Zhang, Z.; Yang, Y.; Wang, Y.; Yang, L.; Li, Q.; Chen, L.; Xu, D. Revealing the A-Site Effect of Lead-Free A<sub>3</sub>Sb<sub>2</sub>Br<sub>9</sub> Perovskite in Photocatalytic C(Sp<sup>3</sup>)–H Bond Activation. *Angew. Chem.* 2020, 132, 18293–18296.

---

## Keywords

perovskite;photocatalyst;organic synthesis;nanocrystals;lead-free;bulk;oxidation;alkylation;polymerization

---

Retrieved from <https://encyclopedia.pub/13665>