

Polyethylene Composites

Subjects: [Polymer Science](#)

Contributor: Erfan Rezvani Ghomi

Polyethylene (PE) is one of the most used plastics worldwide for a wide range of applications due to its good mechanical and chemical resistance, low density, cost efficiency, ease of processability, non-reactivity, low toxicity, good electric insulation, and good functionality.

polyethylene

1. Introduction

In recent times, polymers have been used in a wide range of industrial applications, such as packaging, electronics, and construction [1][2]. To better the performance of the aforementioned applications, polymers need to be more environmentally friendly, safe, and durable [3]. The utilization of polymers is encouraged due to good functionality, acceptable durability, and cost-efficiency; however, high flammability, and poor thermal properties are noticeable limitations for their applicability [4]. Most polymers are flammable and, by exposure to enough energy, they will leave a considerable amount of smoke and heat [5]. It is reported that annually about 5000 people in Europe and 4000 people in the United States are killed by fires. Furthermore, the economic loss of these fire accidents is estimated to be about 0.3% of the GDP [6]. Following the analysis conducted by the Geneva-based Aircraft Crashes Record Office (ACRO), it is possible to reduce the possibility of fire catastrophes and their subsequent fatalities by reducing the flammability of polymeric materials [6]. Therefore, related to the use of polymers, there are environmental, economic, and health issues that are considered as the driving forces to motivate the conduction of research and different studies on the flammability of polymers [7].

Polyolefins are a group of the most popular polymers in various applications [8]. One of the main polymers of this group is PE, with more than 100 million tons production per year, that is, 34% of the total plastic market, and is extensively used due to good mechanical and chemical resistance, low density, cost efficiency, ease of processability, non-reactivity, low toxicity, good electric insulation, and good functionality [9]. However, like other polymers, the concern about PE is its flammability in applications requiring good flame retardancy. Although the emissions from PE have low toxicity, it has a low limiting oxygen index (LOI) and drips during burning, which causes rapid flame spread [10].

Typically, physical or chemical modifications, as well as applying FRs, are recommended to reduce the flammability of PE products [11]. Flame retardancy of polymers increases by incorporation of FRs and is estimated to triplicate their survival time in case of fire [12]. FRs are necessary as they enhance the flammability of polymeric materials by delaying the fire and its spread [13]. The common commercial FRs used for PE systems are based on phosphorus,

borate, inorganic hydroxides, silicon, and nitrogen and are introduced to polymer matrixes during processing [14]. Each of the FR approaches uses a different mechanism and their application is attributed to the polymer matrix and the intended usage. For example, regarding the inorganic hydroxides, they will reduce the burning rate by releasing water to decrease the temperature since decomposition occurs at higher temperatures. Although gas-phase reactions are important in controlling flames in PE systems, quenching FRs based on halogens are not recommended due to environmental concerns [15]. Moreover, intumescent flame retardants (IFRs) are of great importance and efficiency in restricting the fire by forming a swollen char and are applicable for polymeric materials [16]. Considering the high production and applicability of PE, the issue of its flammability is of great importance and hence, there is an urgent need to develop strategies that minimize the flammability of PE.

2. PE Grades and Properties

PEs are one of the most potential materials of value-adding in the case of accurate formulation modifications [17]. It is of great importance to know the grades of PE as their flame performance is correlated with their chemical structure (i.e., branching type) and FR formulations [17]. The structure and properties of PE main grades, including density, crystallinity, LOI, thermal conductivity, melting temperature, and molecular weight are summarized in [Table 1](#).

Table 1. Different properties of PE's grades [18][19][20].

PE Grades	Structure's Description	Density (g/cm ⁻³)	Crystallinity	LOI (%)	Thermal Conductivity (W/m·K)	Melt Temperature (°C)	Mw (g/mol)
LDPE (Low-density PE)	Branched structure containing long and short chains	0.915–0.932	Lower degree of crystallinity	17–18	0.32–0.35	105–115	<50,000
LLDPE (Linear low-density PE)	Branched structure containing short chains	0.910–0.930	Slightly higher than LDPE	17–18	0.35–0.45	120–130	<50,000
HDPE (High-density PE)	Linear structure	0.940–0.970	Higher degree of crystallinity	17–18	0.45–0.5	128–136	Up to 200,000

References

3. The Role of Nanotechnology in Flame Retardancy of Polymer Nanocomposites

L. K. Roy, S. Lu, M. H. Ge, S. P. Jiang, and S. Synergistic effect of zeolite 4A on thermal, mechanical and flame retardant properties of intumescent flame retardant HDPE composites.

Novel Polymer Testing 2020, 81, 1061-1077, doi:https://doi.org/10.1016/j.polytest.2019.1061-1077

properties, such as impact strength and stiffness [21][22]. First, the employment of nanocomposites as FRs is receiving great attention because of nanomaterials with high aspect ratio, and many studies are conducted in this field [23]. Although some of the research in this field indicated improvement of flame retardancy via the incorporation of nanomaterials, some of them showed negative effects of using them [24][25][26]. Recently, researchers turned to the simultaneous use of nanomaterials and FRs to improve the flammability of polymer nanocomposites. Enormous studies have been conducted about the combination of nanomaterials and FR compounds, which showed synergistic effects in different properties of nanocomposites [27][28][29]. Exploiting the combination of these nanoscale materials not only reduces the loading of nanomaterials and FR additives but also improves the mechanical and flame retardancy properties simultaneously.

3. Neisiany, R.E.; Enayati, M.S.; Kazemi-Beydokhti, A.; Das, P.; Ramakrishna, S. Multilayered Bio-Based Electrospun Membranes: A Potential Porous Media for Filtration Applications. *Frontiers in Materials*, 2020, 7, 67, doi:10.3389/fmats.2020.00067

4. Salasinska, K.; Mizera, K.; Cellinski, M.; Kozikowski, P.; Borucka, M.; Gajek, A. Thermal properties and fire behavior of polyethylene with a mixture of copper phosphate and melamine phosphate as a novel flame retardant. *Fire Safety Journal* 2020, https://doi.org/10.1016/j.firesaf.2020.103137, 103137, doi:https://doi.org/10.1016/j.firesaf.2020.103137.

3.1. The Role of Nanomaterials in Improving Flame Retardancy of PE Systems

5. Stachak, P.; Neisiany, R.; Capazza, J.A.; Dong, Y.; Neisiany, E.R.; Pelcastre, L.; Jiang, L.; Xu, Q.; Ramakrishna, S. The need for fully hydrophobic fabrics to counter the results of outbreaks. *Applied Perspectives Science of the Total Environment* 2020, 2, 1396-1410, doi:https://doi.org/10.1016/j.cptec.2020.100901

6. Majka, T.M.; Stachak, P. The studies on the production of polyethylene film with reduced flammability. In *Proceedings of The 21st International Electronic Conference on Synthetic Organic Chemistry*. Chuang et al. also found that the incorporation of nano-dispersed layered silicate and low smoke non-halogen

7. Babu, F.K.; Reddy, G.P.; Priya, M.; Ravi, K.; N. K. Jagan, P. The effect of plasticizer, flame retardant and smoke suppressant on the flame retardancy of FR-EVA/LDPE. *Journal of Applied Polymer Science* 2015, 113, 22-31, doi:https://doi.org/10.1016/j.jap.2015.01.009

8. Lai, X.; Tang, S.; Li, H.; Zeng, X. Flame-retardant mechanism of a novel polymeric intumescent flame retardant containing caged bicyclic phosphate for polypropylene. *Polymer Degradation and Stability* 2015, 113, 22-31, doi:https://doi.org/10.1016/j.jap.2015.01.009

9. Wang, D.; Yeh, Y.; Wang, Y.; Zhang, Y.; Wu, J.; Hu, T.; Peng, D. Fire retardancy of a reactive extruded intumescent flame retardant polyethylene system enhanced by metal chelates. *Polymer Degradation and Stability* 2007, 92, 1592-1598, doi:https://doi.org/10.1016/j.polydegradstab.2007.04.015

10. Liu, Y.; Wang, D.-Y.; Wang, J.-S.; Song, Y.-P.; Wang, Y.-Z. A novel intumescent flame-retardant LDPE system and its thermo-oxidative degradation and flame-retardant mechanisms. *Polymers for Advanced Technologies* 2008, 19, 1566-1575, doi:10.1002/pat.1171.

11. Xu, W.; Zhang, B.; Wang, X.; Wang, G.; Ding, D. The flame retardancy and smoke suppression effect of a hybrid Ni containing CuMoO4 modified reduced graphene oxide/layered double hydroxide on epoxy resin. *Journal of Hazardous Materials* 2018, 343, 364-375, doi:https://doi.org/10.1016/j.jhazmat.2017.09.057.

12. Xu, W.; Zhang, B.; Wang, X.; Wang, G.; Ding, D. The flame retardancy and smoke suppression effect of a hybrid Ni containing CuMoO4 modified reduced graphene oxide/layered double hydroxide on epoxy resin. *Journal of Hazardous Materials* 2018, 343, 364-375, doi:https://doi.org/10.1016/j.jhazmat.2017.09.057.

13. Xu, W.; Zhang, B.; Wang, X.; Wang, G.; Ding, D. The flame retardancy and smoke suppression effect of a hybrid Ni containing CuMoO4 modified reduced graphene oxide/layered double hydroxide on epoxy resin. *Journal of Hazardous Materials* 2018, 343, 364-375, doi:https://doi.org/10.1016/j.jhazmat.2017.09.057.

14. Xu, W.; Zhang, B.; Wang, X.; Wang, G.; Ding, D. The flame retardancy and smoke suppression effect of a hybrid Ni containing CuMoO4 modified reduced graphene oxide/layered double hydroxide on epoxy resin. *Journal of Hazardous Materials* 2018, 343, 364-375, doi:https://doi.org/10.1016/j.jhazmat.2017.09.057.

15. Xu, W.; Zhang, B.; Wang, X.; Wang, G.; Ding, D. The flame retardancy and smoke suppression effect of a hybrid Ni containing CuMoO4 modified reduced graphene oxide/layered double hydroxide on epoxy resin. *Journal of Hazardous Materials* 2018, 343, 364-375, doi:https://doi.org/10.1016/j.jhazmat.2017.09.057.

16. Xu, W.; Zhang, B.; Wang, X.; Wang, G.; Ding, D. The flame retardancy and smoke suppression effect of a hybrid Ni containing CuMoO4 modified reduced graphene oxide/layered double hydroxide on epoxy resin. *Journal of Hazardous Materials* 2018, 343, 364-375, doi:https://doi.org/10.1016/j.jhazmat.2017.09.057.

17. Xu, W.; Zhang, B.; Wang, X.; Wang, G.; Ding, D. The flame retardancy and smoke suppression effect of a hybrid Ni containing CuMoO4 modified reduced graphene oxide/layered double hydroxide on epoxy resin. *Journal of Hazardous Materials* 2018, 343, 364-375, doi:https://doi.org/10.1016/j.jhazmat.2017.09.057.

18. Xu, W.; Zhang, B.; Wang, X.; Wang, G.; Ding, D. The flame retardancy and smoke suppression effect of a hybrid Ni containing CuMoO4 modified reduced graphene oxide/layered double hydroxide on epoxy resin. *Journal of Hazardous Materials* 2018, 343, 364-375, doi:https://doi.org/10.1016/j.jhazmat.2017.09.057.

12. Majlingova, A.; Kačíková, D.; Xu, Q.; Jin, C. Current trends in flame-retardant treatment of selected polymers – a review; Technical University in Zvolen, Slovakia, Republic: 2018.

13. Lim, K.-S.; Ben, S.-T.; Sim, L.T.; Tee, T. T.; Ratnam, C.T.; Hui, D.; Rahman, M.B. A review of application of ammonium polyphosphate as intumescent flame retardant in thermoplastic composites. *Composites Part B: Engineering* 2016, 84, 155-174, doi:https://doi.org/10.1016/j.compositesb.2015.08.066.

14. Gao, H.; Hu, S.; Han, H.; Zhang, J. Effect of different metallic hydroxides on flame-retardant properties of low density polyethylene/melamine polyphosphate/starch composites. *Journal of Applied Polymer Science* 2011, 122, 3263-3269, doi:10.1002/app.34398.

15. Camino, G.; Grassie, N.; McNeill, I.C. Influence of the fire retardant, ammonium polyphosphate, on the thermal degradation of poly(methyl methacrylate). *Journal of Polymer Science: Polymer Chemistry Edition* 1978, 16, 95-106, doi:10.1002/pol.1978.170160115.

16. Dasari, A.; Yu, Z.-Z.; Cai, G. P.; Mai, Y. W. Recent developments in the fire retardancy of polymeric materials. *Progress in Polymer Science* 2013, 38, 1257-1387, doi:https://doi.org/10.1016/j.progpolymsci.2013.06.006.

17. Luyt, A.S.; Malik, S.S.; Gasmi, S.A.; Porfyris, A.; Andronopoulou, A.; Korres, D.; Vouyiouka, S.; Grosshauser, M.; Pfaendner, R.; Brüll, R. Halogen-free flame-retardant compounds. Thermal decomposition and flammability behavior for alternative polyethylene grades. *Polymers* 2019, 11, 1479.


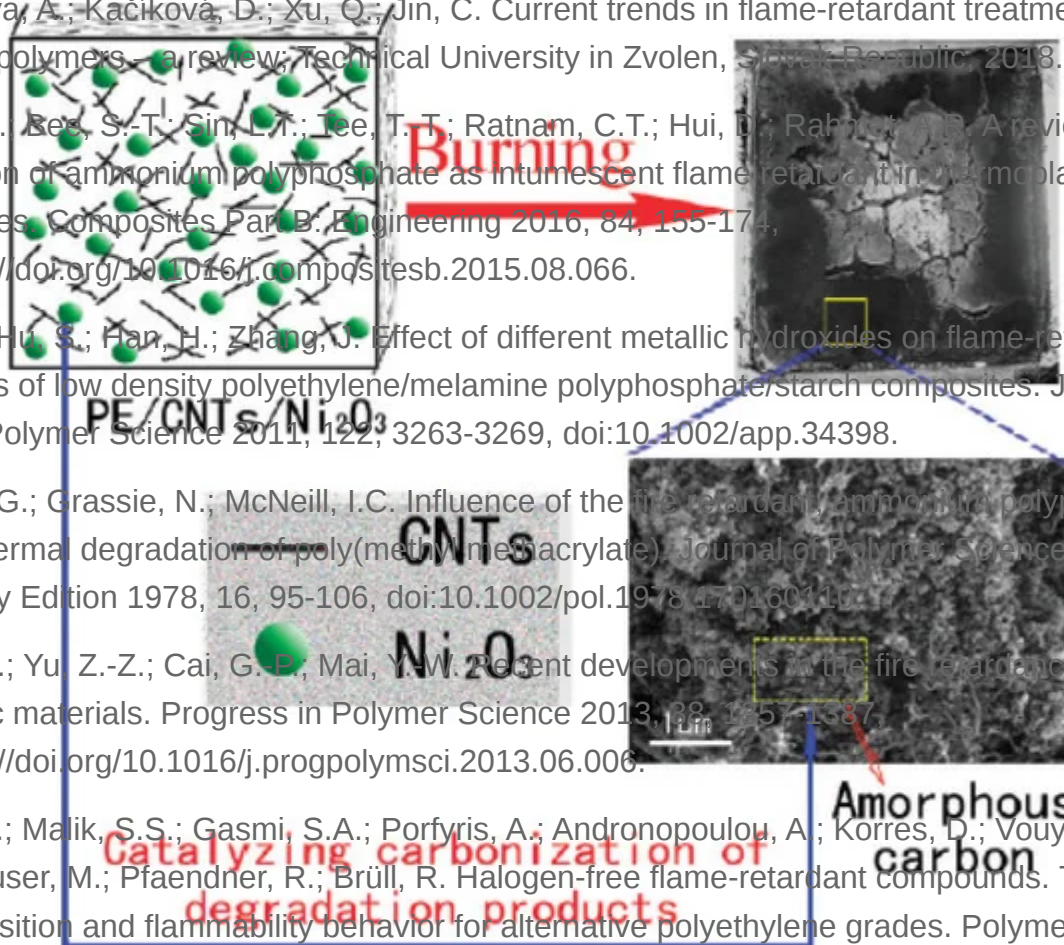


Figure 1. Schematic representation of the synergistic effect mechanism between NiO and MWCNTs on enhancing the flame retardancy of LDPE; reprinted with permission from Ref. [32].

19. Hench, L.; Jones, J. *Biomaterials, artificial organs and tissue engineering*; Elsevier, Abington, USA: 2005.

20. Li, D.; Zhou, L.; Wang, X.; He, L.; Yang, X. Effect of Crystallinity of Polyethylene with Different Densities on Breakdown Strength and Conductance Property. *Materials* 2019, 12, doi:10.3390/ma12111746.

21. Sun, D.-x.; Yang, C.-j.; Qi, X.-d.; Yang, J.-h.; Wang, Y. Largely enhanced fracture toughness of the PP/EPDM blends induced by adding carbon nanofibers. *Composites Science and Technology* 2018, 164, 146-152.

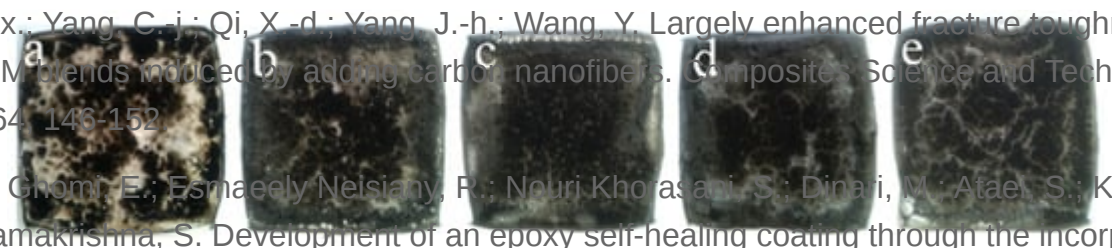

22. Rezvani Ghomi, E.; Esmaeely Neisiany, R.; Nouri-Khorasani, S.; Dinari, M.; Ataei, S.; Koochaki, M.S.; Ramakrishna, S. Development of an epoxy self-healing coating through the incorporation of acrylic acid-co-acrylamide copolymeric gel. *Progress in Organic Coatings* 2020, 149, 105948, doi:https://doi.org/10.1016/j.porgcoat.2020.105948.

Figure 1. Photos of the residues after cone testing (100 x 100 mm²) of PE/ATH/GNP_x, (a), x = 0.2 (b), x = 0.5 (c), x = 1.0 (d), and x = 1.5 (e), reprinted with permission from Ref. [33].

23. Kashiwagi, T.; Du, F.; Douglas, J.F.; Winey, K.I.; Harris, R.H.; Shields, J.R. Nanoparticle networks **Table 2** reports the flammability of polymer/nanocomposites. *Nature materials* 2005, 4, 928-933.

Table 2. Effect of FR, nanomaterials, FR, and nanomaterials on the flame-retardant properties of PE; Lopez-Cuesta, J.M.; Nagy, J.B.; Alexandre, M.; Dubois, P. Mechanical properties and flame-retardant behavior of ethylene vinyl

Nanomaterial and Its Loading Amount	Types of FR and Its Loading	Result(s)
Ce-MWCNTs, 3 wt.%	Brominated FR, 10 wt.%	25% reduction in PHR rate observed from CCT, improved the UL-94 from V-2 to V-0
Nano-SiO ₂ , 6 wt.%	APP, 8 wt.%	42% and 44% reduction in average HRR and PHR rate, respectively, 78% increase in TTI
Organic-modified montmorillonite, 10 wt.%	MHSH, 30 wt.%	84% reduction in PHR rate and increase in t_{ign} observed from CCT.
Organic-modified montmorillonite, 5 wt.%	IFRs, 15 wt.%	51% reduction in PHR rate observed from CCT
Halloysite nanotubes, 2 wt.%	IFRs, 28 wt.%	92% and 75% decrease in PHR rate and THR, respectively.
Graphene, 1 wt.%	Brominated polystyrene/antimony trioxide, 6.2 wt.%	Increase LOI value from 23.4% to 24.1%, change UL-94 grades from NG to V-2.

29. Huang, G.; Chen, S.; Song, P.; Lu, P.; Wu, C.; Liang, H. Combination effects of graphene and layered double hydroxides on intumescent flame-retardant poly (methyl methacrylate) nanocomposites. *Applied Clay Science* 2014, 88, 78-85.

3.2. Incorporation Methods of Nanomaterials in Polymer Matrices

30. Szustakiewicz, K.; Cichy, B.; Gazińska, M.; Piękowski, J. Comparative study on flame, thermal, and mechanical properties of HDPE/clay nanocomposites with MPP or APP. *Journal of Reinforced Plastics and Composites* 2013, 32, 1005-1017.

A variety of methods are applied for the incorporation of nanomaterials into PE depending on the nature of the nanomaterials [34]. These methods include in situ polymerization, solvent casting, and melt mixing, which will be elaborated in the following sections.

31. Chuang, T.-H.; Guo, W.; Cheng, K.-C.; Chen, S.-W.; Wang, H.-T.; Yen, Y.-Y. Thermal properties and flammability of ethylene-vinyl acetate copolymer/montmorillonite/polyethylene nanocomposites with flame retardants. *Journal of Polymer Research* 2004, 11, 169-174.

3.2.1. In Situ Polymerization

In this method, at first nanomaterials and monomers are mixed in a solvent with a proper shear rate, which obtains a stable suspension [35]. In this stage, some interfacial agents are added to enhance the stability of the mixture simultaneously improving the flame retardancy and mechanical properties of polyethylene. Then, the obtained mixture is fed to the reactor where the processing conditions mostly are the same applied to the synthesis of the base polymer. When the polymerization is complete, the solvent is removed [36]. This method is used for a wide range of polymeric nanocomposites.

33. Han, Z.; Wang, Y.; Dong, W.; Wang, P. Enhanced fire retardancy of polyethylene/alumina trihydrate composites by graphene nanoplatelets. *Materials Letters* 2014, 128, 275-278.

4.2.2. Solvent Casting

34. Visakh, P.; Yoshihiko, A. *Flame retardants: Polymer blends, composites and nanocomposites*; Springer Nature, Switzerland AG, Gewerbestr. 11, 6330 Cham, Switzerland, 2015.

This method is mostly used in cases that there is not enough dispersion of nanomaterials in the polymer [37]. In other words, the thermodynamic affinity between polymer and filler is not favorable for homogeneous dispersion.

35. Ajayan, P.M.; Schadler, L.S.; Braun, P.V. *Nanocomposite science and technology*, John Wiley & Sons, Weinheim, Germany, 2006.

Therefore, the most important step of this method is the breaking of the agglomerates of nanomaterials, and ultrasonication is the best method to achieve this goal. This process is especially suitable for the exfoliation of clay

36. Aslzadeh, M.M.; Mir Mohamad Sadeghi, G.; Abdouss, M. Synthesis and characterization of chlorine-containing flame-retardant polyurethane nanocomposites via in situ polymerization. layers and thermosetting polymers [38]. To conserve dispersed/intercalated/exfoliated structure, some interfacial compatibilizers, such as maleic anhydride grafted polymers, are used.

4.2.13 Melt Mixing

- Journal of Polymer Science 2012, 123, 437-447.
37. Chung, D. D. Composite materials: science and applications; Springer Science & Business Media, Springer-Verlag London, UK: 2010.
- Melt compounding is the most common method for the production of nanocomposites because of the simplicity and availability of equipment [40,41]. Depending on the amount of the product, an internal mixer and twin-screw extruder are used for processing. There are two major methods of feeding for melt compounding: direct and master-batch which the later method is more common. In the master batch feeding method, first, a concentrated master batch of filler is prepared and then is diluted in the base polymer [42]. To obtain a good dispersion of filler in polymer and improve compatibility among components, some grafted polymers are utilized [43].
38. Kulkarni, B.R.; Nandipati, A.K. Physical, mechanical, and conductivity properties of poly (3-hexylthiophene)-montmorillonite clay nanocomposites produced by the solvent casting method. *Macromolecules* 2004, 37, 8577-8584.
39. Wang, Q.; Dai, J.; Li, W.; Wei, Z.; Jiang, J. The effects of CNT alignment on electrical conductivity, mixing time, temperature, and design of the screw profile can determine the final microstructure and properties of the nanocomposites [44,45]. *Composites science and technology* 2008, 68, 1644-1648.
40. Utracki, L.A.; Wilkie, C.A. Polymer blends handbook; Springer, Netherlands: 2002; Vol. 1.
41. Tadmor, Z.; Gogos, C.G. Principles of polymer processing; John Wiley & Sons, Hoboken, New Jersey, USA: 2013.
42. Markarian, J. Flame retardants for polyamides-new developments and processing concerns. *Plastics, Additives and Compounding* 2005, 7, 22-25.
43. Ghomi, E.R.; Khorasani, S.N.; Kichi, M.K.; Dinari, M.; Ataei, S.; Enayati, M.H.; Koochaki, M.S.; Neisiany, R.E. Synthesis and characterization of TiO₂/acrylic acid-co-2-acrylamido-2-methyl propane sulfonic acid nanogel composite and investigation its self-healing performance in the epoxy coatings. *Colloid and Polymer Science* 2020, 298, 213-223, doi:10.1007/s00396-019-04597-0.
44. Huang, Y.Y.; Terentjev, E.M. Dispersion of carbon nanotubes: mixing, sonication, stabilization, and composite properties. *Polymers* 2012, 4, 275-295.
45. Kasaliwal, G.; Villmow, T.; Pegel, S.; Pötschke, P. Influence of material and processing parameters on carbon nanotube dispersion in polymer melts. In *Polymer-Carbon Nanotube Composites*, Elsevier: 2011; pp. 92-132.

Retrieved from <https://encyclopedia.pub/entry/history/show/17028>