

Conductive Electrospun Nanofiber Mats

Subjects: **Nanoscience & Nanotechnology**

Contributor: Tomasz Blachowicz , Andrea Ehrmann

Conductive nanofiber mats can be used in a broad variety of applications, such as electromagnetic shielding, sensors, multifunctional textile surfaces, organic photovoltaics, or biomedicine. Here we give an overview of the most recent applications of such conductive electrospun nanofiber mats.

electrospinning

conductive nanofibers

conductive solution

conductive polymers

conductive coating

1. Electromagnetic Shielding

One of the large areas in which electrospun nanofiber mats are used is electromagnetic shielding. Typically, lightweight electromagnetic (EM) wave absorbers are prepared as heterogeneous structures from magnetic and dielectric loss materials, with the heterogeneous structure supporting the interaction between an electromagnetic wave and absorber^[1]. This results in a strong use of combinations of magnetic loss materials like magnetic metals with dielectric loss materials like carbon in different modifications for the preparation of lightweight EM composite absorbers, as depicted in Figure 1^{[2][3][4][5]}. Nanofiber mats electrospun from other combinations such as ZnO/C are also reported to show good microwave absorption^[6].

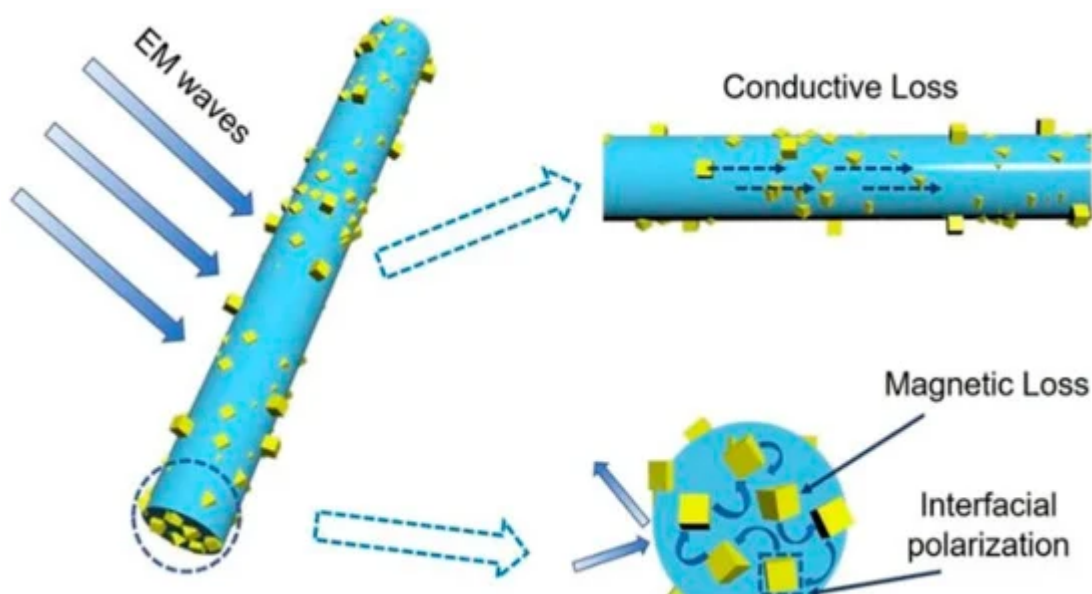


Figure 1. Electromagnetic wave absorption due to magnetic and dielectric losses. Reprinted from , with permission from Elsevier^[2].

2. Energy Storage

Another application of conductive nanofiber mats are electrodes of lithium-ion batteries. Here again, metallic and carbon-based materials are often combined to gain a sufficient conductivity. Typically, the anode is prepared from MgFe_2O_4 in combination with graphene^[7], carbon nanotubes^[8] or graphene aerogel^{[9][10]}. MoS_2 /carbon nanofiber membranes were prepared by needle-based electrospinning and carbonization of the PAN-based precursor and used as binder-free anodes for sodium-ion batteries^[11].

Interlayers for Li-S batteries were prepared by Zhang et al., combining a reduced graphene oxide layer with BaTiO_3 decorated carbon nanofibers prepared by electrospinning and subsequent calcination (Fig. 2), resulting in low resistances around $30\ \Omega$ in the fresh state and around $6\ \Omega$ after cycling, resulting in a high rate performance and cycling performance^[12].

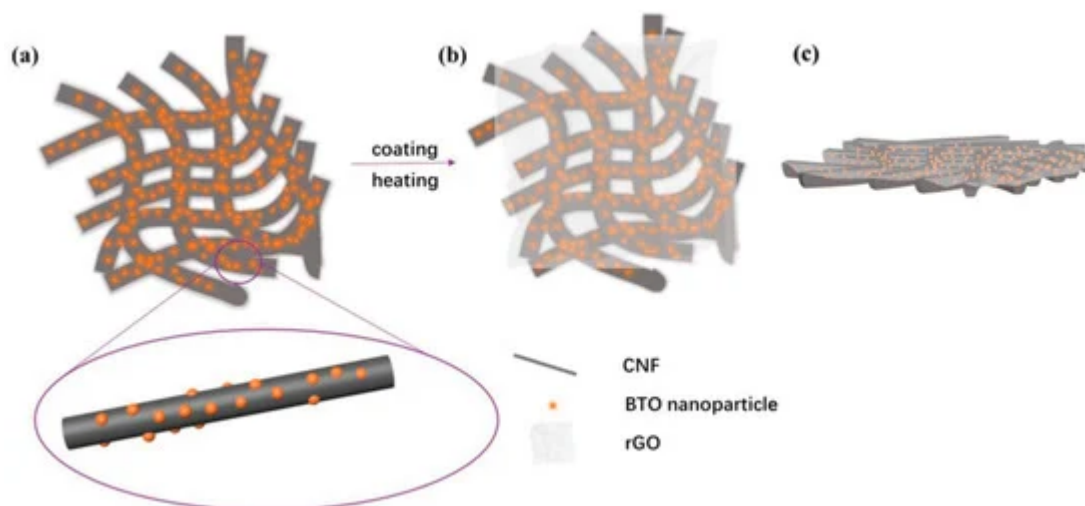


Figure 2. Pure BaTiO_3 @CNF interlayer and interlayer loaded with rGO. Reprinted from^[12], with permission from WILEY-VCH Verlag GmbH & Co. KGaA. (a) BaTiO_3 @CNF interlayer; (b) $\text{rGO}/\text{BaTiO}_3$ @CNF interlayer in top view; (c) $\text{rGO}/\text{BaTiO}_3$ @CNF interlayer in side view.

Supercapacitors, on the other hand, can be created by firstly electrospinning TiO_2 nanofibers from a solution of $\text{Ti}(\text{OC}_4\text{O}_9)_4$ and poly(vinyl pyrrolidone) (PVP), followed by calcination to remove the polymer and retain the pure semiconductive nanofibers. Next, nitridization via ammonia annealing resulted in highly conductive TiN nanofibers. These nanofibers were afterward coated with MnO_2 nanosheets, resulting in increased specific capacitance and cycle stability^[13].

3. Electronic Components

Even memristors were produced by conductive nanofiber mats. Lapkin et al. used electrospinning to produce polyamide-6 nanofiber mats on which PANi was polymerized, resulting in a conductivity around 1 S/cm. Combined with a solid polymer electrolyte and a silver counter electrode, a memristor could be realized which showed resistive switching due to a voltage-controlled change in the PANi redox state^[14]. Döpke et al. suggested producing conductive magnetic nanofiber mats for data storage and transfer^[15].

4. Tissue Engineering and Cell Growth

Tissue engineering generally is often based on electrospun nanofiber mats. In order to engineer cardiac tissue, it is not only necessary to create porous nanofiber scaffolds, but these scaffolds should also mimic the extra-cellular matrix of the target tissue, i.e., should be conductive in case of growing cardiac muscle tissue on them with undisturbed intracellular signaling^{[16][17]}. In general, scaffolds with embedded conductive materials often show advances against non-conductive nanofiber mats, whether prepared with PANi, PPy or CNTs^{[18][19][20]}.

Nekouian et al. report on conductive electrospun nanofiber mats, prepared from PCL/PPy/multi-wall CNTs which were used to examine the influence of electrical stimulation on the photoreceptor differentiation of mesenchymal stem cells, showing that rhodopsin and peripherin gene expressions could significantly be increased by the electrical stimulation^[21]. Rahmani et al. used silk fibroin nanofibers filled with conductive reduced graphene oxide, resulting in electrochemical series resistances around 20–30 Ω , to grow conjunctiva mesenchymal stem cells under electrical stimulation and found formation of neuron-like cell morphology and alignment along the electrical field^[22]. PCL/PANi scaffolds with conductivities up to approximately 80 $\mu\text{S}/\text{cm}$ were used by Garrudo et al. for the cultivation of neural stem cells, showing that the typical cell morphology was retained, and the nanofiber mats were biocompatible^[23]. Even lower values of approximately 1 $\mu\text{S}/\text{cm}$ were reported by Ghasemi et al. who doped electrospun polyethylene terephthalate (PET) nanofibers with graphene oxide to prepare cardiac patches for cardiac regeneration after myocardial infarcts^[24]. For the same purpose, Walker et al. suggested using electrospun gelatin methacryloyl with bio-ionic liquid to combine adhesive and conductive properties^[25].

Cell proliferation and gene expression could also be optimized by doping PANi scaffolds with graphene oxide and plasma treatment to hydrophilize the fiber surface^[26]. Attachment, spreading and proliferation of fibroblasts and endothelial cells was optimized by tailoring the concentration of multilayer graphene flakes in electrospun polyurethane nanofiber mats^[27]. Embedding reduced graphene oxide in electrospun poly(ester amide) (PEA) and PEA/chitosan scaffolds increased cardiac differentiation^[28]. Similarly, electrospinning PEO/PEDOT:PSS nanofibers showed a positive effect on neurite outgrowth, i.e., neural differentiation of neuron-like model cells, which is especially interesting since a spin-coated PEO/PEDOT:PSS film showed contact repulsion limiting cell attachment and proliferation (Figure 3)^[29].

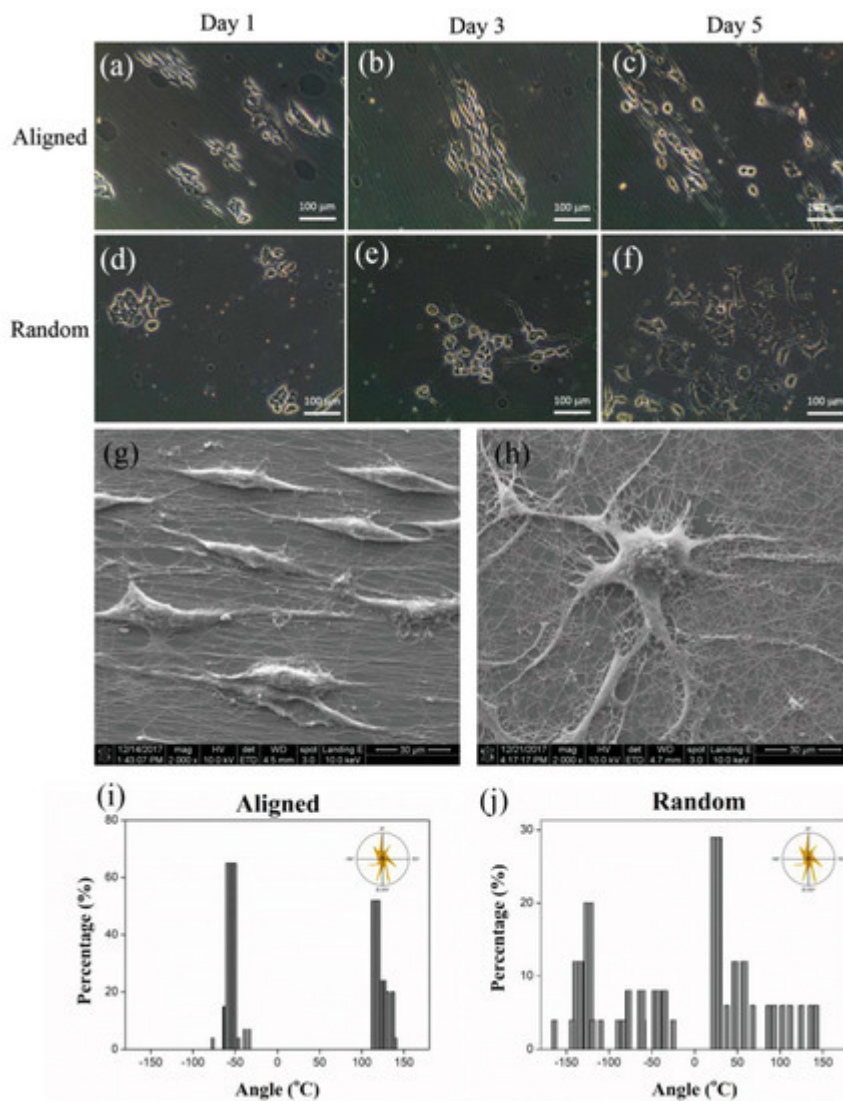


Figure 3. PC12 cells grown on aligned (a–c,g) and random nanofibers (d–f,h), resulting in oriented or random neurites (i,j). Reprinted from [29], with permission from WILEY-VCH Verlag GmbH & Co. KGaA.

Osteoblast cells were found to grow and proliferate well on electrospun poly(L-lactic acid)/PAni/p-toluene sulfonic acid nanofiber mats [30]. Keratinocytes were shown to grow on electrospun PAN/PPy and PAN/PPy/CNT nanofiber mats [31]. Coating electrospun polyurethane nanofibers with PAni reduced the water contact angle significantly, resulted in a certain anticoagulant effect and was found supportive for cell adhesion, proliferation, and extension [32].

5. Dye-Sensitized Solar Cells

Counter electrodes of dye-sensitized solar cells (DSSCs) were prepared by coating an electrospun nanofiber mat with PEDOT:PSS. Juhász Junger et al. used several dip-coating steps to optimize the electrode conductivity while partly retaining the nanostructured surface and thus the large contact area with the neighboring layers (Fig. 4) [33]. The optimum number of layers resulted in a sheet resistance around 150 Ω , reduced from approximately 550 Ω for

a single coating layer^{[33][34]}. A similar approach was recently suggested by Kohn et al. who prepared fully electrospun DSSCs with both electrodes prepared by separately dip-coating them in PEDOT:PSS^[35].

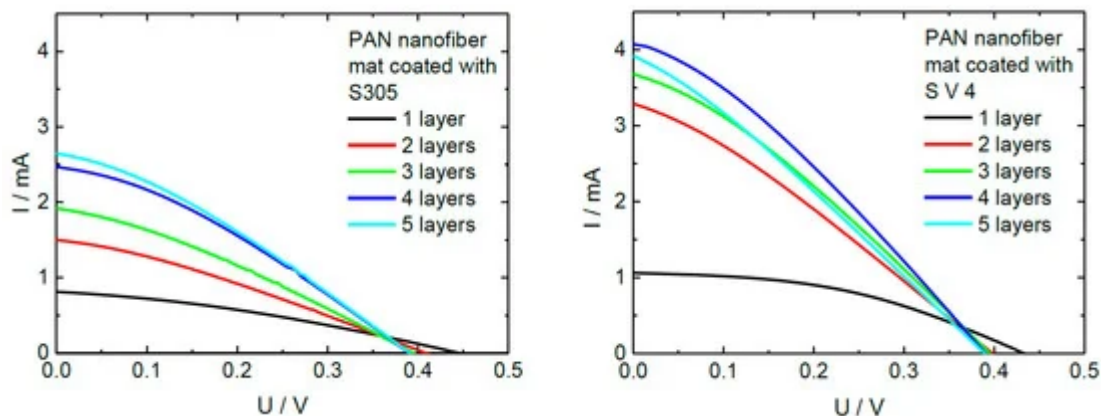


Figure 4. Current-voltage curves of DSSCs, prepared with different PEDOT:PSS counter electrodes. Reprinted from^[33], originally published under a CC BY license.

Eslah and Nouri, on the other hand, used spin-coating of WO_3 nanoparticles on electrospun PAN/PAni nanofibers to prepare counter electrodes of DSSCs^[36]. For the possible use in LEDs and solar cells, Jiang et al. developed transparent conductive electrodes by electrospinning copper nanofibers and immersing them in silver ink as a protective layer, resulting in sheet resistances below 10Ω ^[37].

6. Hydrogen Evolution

Another interesting application is hydrogen evolution. Sun et al. most recently prepared electrospun carbon/Ni/ Mo_2C nanofibers which were used as electrocatalysts in hydrogen evolution reaction in an alkaline electrolyte^[38]. Li et al. used nitrogen-doped carbon/Ni nanofibers decorated with Pt for hydrogen evolution, resulting in a high electrochemical activity combined with reduced usage of Pt^[39]. Zhang et al. prepared binder-free MoS_2 /carbon nanofiber electrodes by electrospinning and carbonization of the resulting nanofibers, allowing them to tailor the porosity chemically, which could be used for electrocatalytic hydrogen production^[40]. Rheem et al. used a hierarchical structure of MoS_2 nanosheets on conductive MoO_2 nanofibers, gained by electrospinning, calcination, and sulfurization, to increase the hydrogen evolution reaction^[41]. A similar hierarchical structure was prepared earlier by Liu et al. who used porous electrospun TiO_2 nanofibers as a substrate for growing MoS_2 nanosheets perpendicular to the nanofiber surfaces, resulting in high photocatalytic hydrogen production (Figure 5)^[42].

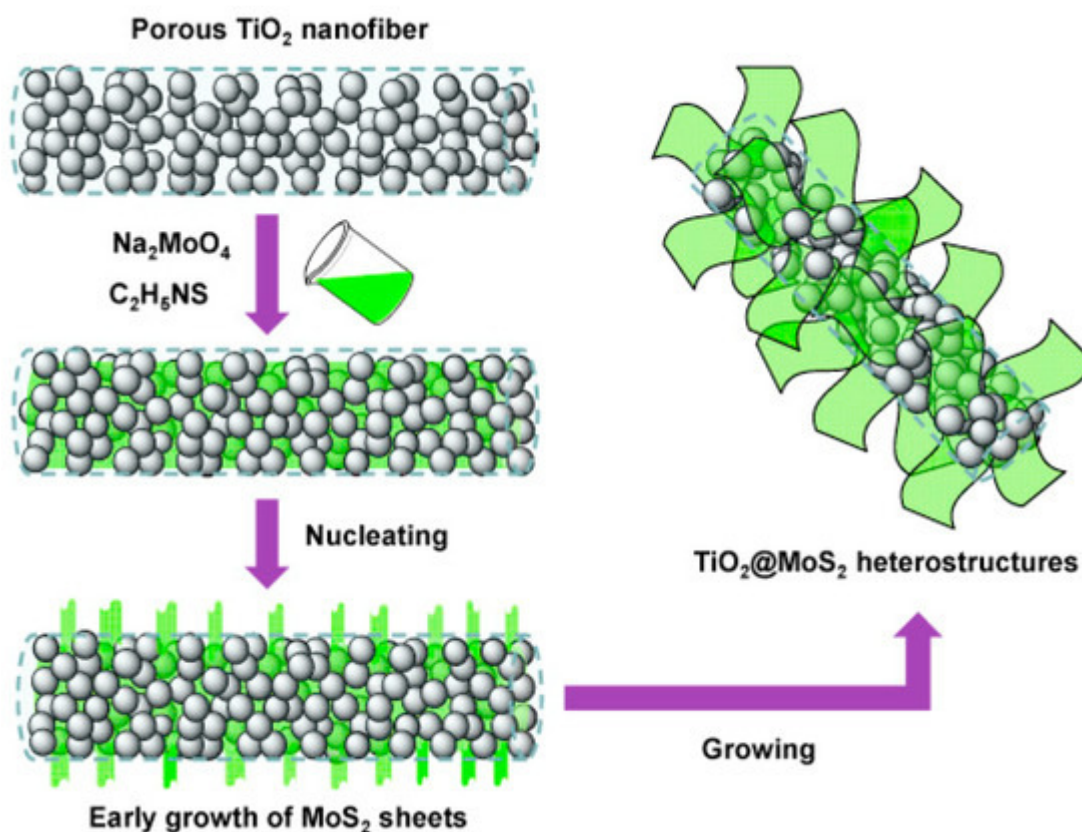


Figure 5. Nucleation and growth of MoS_2 nanosheets on porous TiO_2 nanofibers. Reprinted from^[42], with permission from Elsevier.

7. Sensors

Lee et al. used electrospun WO_3 nanofibers coated with RuO_2 nanorods as a sensor for H_2O_2 and L-ascorbic acid. They could show that by the addition of the RuO_2 nanorods, the electrocatalytic activity was increased, and the sensing abilities were significantly improved in comparison with pure WO_3 nanofibers, as shown in Figure 6^[43].

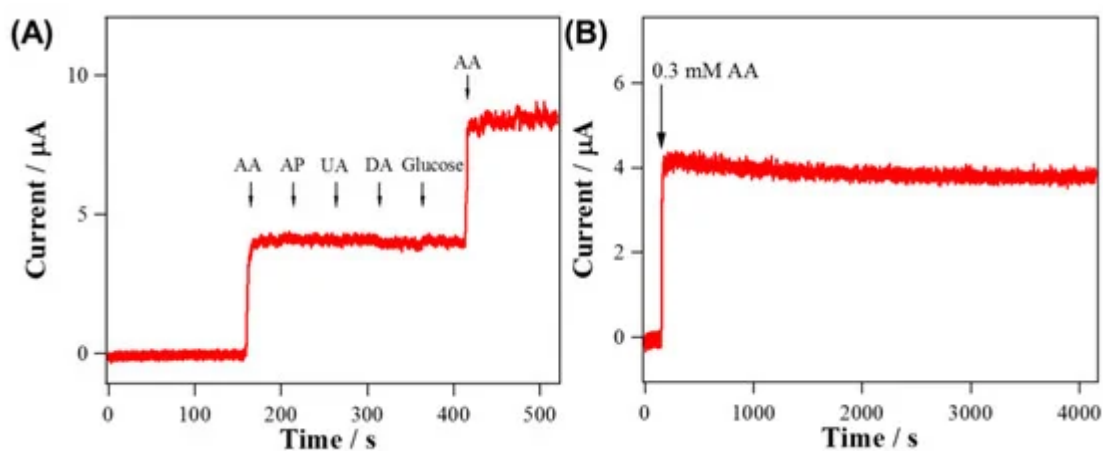


Figure 6. The amperometric response of the WO_3 nanofiber with RuO_2 nanorods, showing the stability for detection of L-ascorbic acid (AA) against additions of diverse chemicals (A) and against time (B). Reprinted

from[43], originally published under a CC BY license.

To sense dopamine, Ozoemena et al. used electrospun PAN/onion-like carbon nanofibers and found a high conductivity and sensitivity of the resulting nanofibers[44]. By electrospinning polystyrene/polyhydroxybutyrate filled with graphitized carbon and partly doped with porphyrin on an interdigitated electrode, Avossa et al. prepared gas sensors for volatile organic compounds[45].

Shaker et al. developed a polyurethane/PEDOT:PSS electrospun nanofiber mat which exhibited a resistance of approximately 3 kΩ and could be used as a reliable strain gauge sensor[46]. Yang et al. coated highly conductive MXene sheets on electrospun PU nanofibers mats to produce highly sensitive strain sensors[47]. Flexible strain sensors with up to 1000% elongation were prepared from conductively coated electrospun styrenebutadiene-styrene copolymer[48]. A similar stretchability was reached by Ren et al., electrospinning a thermoplastic polyurethane nanofiber mat with a wavelike structure, followed by wrapping CNTs around the nanofibers[49]. Wrapping conductive nanofiber yarn produced from graphene oxide-doped PAN nanofibers with in-situ polymerized PPy around elastic yarns results in high sensitivity and repeatability, in this way enabling detection or breathing or human motion[50].

Harjo et al. developed conductive fiber scaffolds by coating electrospun glucose-gelatin nanofiber mats with polypyrrole and investigated their electro-chemo-mechanical response, showing stable actuation for more than 100 cycles as well as reasonable sensor properties[51]. They found conductivities of approximately 3 μS/cm in the unstretched state and approximately half this value when stretched in aqueous or organic electrolyte solutions.

Table 1. Examples of electrical conductivities of nanofiber mats mentioned in this paper, sorted by conductivity.

Nanofiber Materials	Conductivity/(S/cm)	Ref.
PVA/polyaniline	0.35×10^{-9}	[52]
Multi-wall CNTs in polystyrene	10^{-8}	[53]
Polypyrrole/poly(butyl acrylate-co-methyl methacrylate)	0.5×10^{-6}	[54]
Polyethylene terephthalate/graphene oxide	1×10^{-6}	[24]
Glucose-gelatin coated with polypyrrole	3×10^{-6}	[32]

Multi-wall CNTs in a polyurethane/silk	60×10^{-6}	[55]
PCL/PAni	80×10^{-6}	[23]
Camphoric acid doped PAni/poly(ethylene oxide)	10^{-6} – 10^{-4}	[56]
PAN coated with multi-wall CNTs	3×10^{-3}	[57]
Multi-wall CNTs/polyurethane	10^{-5} – 10^{-2}	[58]
Poly(caprolactone)/PAni	10^{-4} – 10^{-1}	[23]
Poly(L-lactide acid) coated with chitosan/ polypyrrole	0.01	[59]
Fe ₃ O ₄ /polylactic acid-glycolic acid coated with pyrrole	0.58	[59]
Graphite in polystyrene	1	[60]
Polyamide-6 nanofiber mats coated with PAni	1	[14]
Trimethylethoxysilane/graphene	20	[61]
PEDOT	60	[62]
PU coated with p-toluenesulfonate doped PPy	276	[63]
Silver nanowires in polyvinyl alcohol	650	[64]
Poly(vinylidene fluoride-co-trifluoro ethylene) coated with	4000	[65]

multi-wall CNTs and reduced graphene oxide

Generally, possible applications of electrospun nanofibers vary from biomedicine to sensors to batteries to hydrogen evolution. Similarly, the range of conductivities achievable with different methods is wide. This entry gives an overview of some recent applications.

References

1. Xiaofang Liu; Chengcheng Hao; He Jiang; Min Zeng; Ronghai Yu; Hierarchical NiCo₂O₄/Co₃O₄/NiO porous composite: a lightweight electromagnetic wave absorber with tunable absorbing performance. *Journal of Materials Chemistry C* **2017**, 5, 3770-3778, 10.1039/C6TC05167G.
2. Meng, X.F.; Dong, S.H. Design and construction of lightweight C/Co heterojunction nanofibers for enhanced microwave absorption performance. *J. Alloys Compd.* 2019, 810, 151806.
3. Wanxi Li; Hongxue Qi; Fang Guo; Yien Du; Ningjing Song; Yanyun Liu; Yongqiang Chen; Co nanoparticles supported on cotton-based carbon fibers: A novel broadband microwave absorbent. *Journal of Alloys and Compounds* **2019**, 772, 760-769, 10.1016/j.jallcom.2018.09.075.
4. Fengyi Wang; Yunqiang Sun; Deren Li; Bo Zhong; Zhiguo Wu; Shiyong Zuo; De Yan; Renfu Zhuo; Juanjuan Feng; Pengxun Yan; Microwave absorption properties of 3D cross-linked Fe/C porous nanofibers prepared by electrospinning. *Carbon* **2018**, 134, 264-273, 10.1016/j.carbon.2018.03.081.
5. Huihui Liu; Yajing Li; Mengwei Yuan; Genban Sun; Qingliang Liao; Yue Zhang; Solid and macroporous Fe₃C/N-C nanofibers with enhanced electromagnetic wave absorbability. *Scientific Reports* **2018**, 8, 16832, 10.1038/s41598-018-35078-z.
6. Weihua Gu; Jing Lv; Bin Quan; Xiaohui Liang; Baoshan Zhang; Guangbin Ji; Achieving MOF-derived one-dimensional porous ZnO/C nanofiber with lightweight and enhanced microwave response by an electrospinning method. *Journal of Alloys and Compounds* **2019**, 806, 983-991, 10.1016/j.jallcom.2019.07.334.
7. Yanhong Yin; Wenfeng Liu; Ningning Huo; Shuting Yang; Synthesis of Vesicle-Like MgFe₂O₄/Graphene 3D Network Anode Material with Enhanced Lithium Storage Performance. *ACS Sustainable Chemistry & Engineering* **2017**, 5, 563-570, 10.1021/acssuschemeng.6b01949.
8. Clara Pereira; Rui S. Costa; Laury Lopes; Belen Bachiller-Baeza; Inmaculada Rodríguez-Ramos; Antonio Guerrero-Ruiz; Pedro B. Tavares; Cristina Freire; André M. Pereira; Multifunctional mixed valence N-doped CNT@MFe₂O₄ hybrid nanomaterials: from engineered one-pot coprecipitation

- to application in energy storage paper supercapacitors. *Nanoscale* **2018**, *10*, 12820-12840, 10.1039/c8nr03533d.
9. Lei Luo; Zhi Chen; Huizhen Ke; Sha Sha; Guangming Cai; Dawei Li; Hongjun Yang; Xiaowei Yang; Ruquan Zhang; Jianqiang Li; et al. Yonggui LiJie XuWeilin XuQufu Wei Facile synthesis of three-dimensional MgFe₂O₄/graphene aerogel composites for high lithium storage performance and its application in full cell. *Materials & Design* **2019**, *182*, 108043, 10.1016/j.matdes.2019.108043.
 10. Emery Brown; Pengli Yan; Halil Tekik; Ayyappan Elangovan; Jian Wang; Dong Lin; Jun Li; 3D printing of hybrid MoS₂-graphene aerogels as highly porous electrode materials for sodium ion battery anodes. *Materials & Design* **2019**, *170*, 107689, 10.1016/j.matdes.2019.107689.
 11. Xiaoqin Xiong; Wei Luo; Xianluo Hu; Chaoji Chen; Long Qie; Dongfang Hou; Yunhui Huang; Flexible Membranes of MoS₂/C Nanofibers by Electrospinning as Binder-Free Anodes for High-Performance Sodium-Ion Batteries. *Scientific Reports* **2015**, *5*, 9254, 10.1038/srep09254.
 12. Shaoqiong Zhang; Xianying Qin; Yuanming Liu; Lihan Zhang; Ngqing Liu; Yue Xia; Hua Zhu; Baohua Li; Feiyu Kang; A Conductive/Ferroelectric Hybrid Interlayer for Highly Improved Trapping of Polysulfides in Lithium–Sulfur Batteries. *Advanced Materials Interfaces* **2019**, *6*, 1900984, 10.1002/admi.201900984.
 13. Kaibing Xu; Yuenian Shen; Ke Zhang; Fang Yang; Shijie Li; Junqing Hu; Hierarchical assembly of manganese dioxide nanosheets on one-dimensional titanium nitride nanofibers for high-performance supercapacitors.. *Journal of Colloid and Interface Science* **2019**, *552*, 712-718, 10.1016/j.jcis.2019.05.093.
 14. D.A. Lapkin; S.N. Malakhov; V.A. Demin; S.N. Chvalun; L.A. Feigin; Hybrid polyaniline/polyamide-6 fibers and nonwoven materials for assembling organic memristive elements. *Synthetic Metals* **2019**, *254*, 63-67, 10.1016/j.synthmet.2019.05.016.
 15. Christoph Döpke; Timo Grothe; Pawel Steblinski; Michaela Klöcker; Lilia Sabantina; Dorota Kosmalska; Tomasz Blachowicz; Andrea Ehrmann; Magnetic Nanofiber Mats for Data Storage and Transfer. *Nanomaterials* **2019**, *9*, 92, 10.3390/nano9010092.
 16. Taimoor Hasan Qazi; Ranjana Rai; Dirk Dippold; Judith E. Roether; Dirk W. Schubert; Elisabetta Rosellini; Niccoletta Barbani; Aldo R. Boccaccini; Development and characterization of novel electrically conductive PANI–PGS composites for cardiac tissue engineering applications. *Acta Biomaterialia* **2014**, *10*, 2434-2445, 10.1016/j.actbio.2014.02.023.
 17. Ana M. Martins; George Eng; Sofia G. Caridade; João F. Mano; Rui L. Reis; Gordana Vunjak-Novakovic; Electrically Conductive Chitosan/Carbon Scaffolds for Cardiac Tissue Engineering. *Biomacromolecules* **2014**, *15*, 635-643, 10.1021/bm401679q.

18. Baolin Guo; Peter X. Ma; Conducting Polymers for Tissue Engineering. *Biomacromolecules* **2018**, *19*, 1764-1782, 10.1021/acs.biomac.8b00276.
19. Molamma P. Prabhakaran; Laleh Ghasemi-Mobarakeh; Guorui Jin; Seeram Ramakrishna; Electrospun conducting polymer nanofibers and electrical stimulation of nerve stem cells. *Journal of Bioscience and Bioengineering* **2011**, *112*, 501-507, 10.1016/j.jbiosc.2011.07.010.
20. Yaobin Wu; Ling Wang; Baolin Guo; Peter X Ma; Interwoven Aligned Conductive Nanofiber Yarn/Hydrogel Composite Scaffolds for Engineered 3D Cardiac Anisotropy. *ACS Nano* **2017**, *11*, 5646-5659, 10.1021/acsnano.7b01062.
21. Nekouian, S.; Sojoodi, M.; Nadri, S.; Fabrication of conductive fibrous scaffold for photoreceptor differentiation of mesenchymal stem cell. *J. Cell. Physiol* **2019**, *234*, 15800–15808, 10.1002/jcp.28238.
22. Rahmani, A.; Nadri, S.; Kazemi, H.S.; Mortazavi, Y.; Sojoodi, M; Conductive electrospun scaffolds with electrical stimulation for neural differentiation of conjunctiva mesenchymal stem cells. *Artif. Organs* **2019**, *43*, 780–790, 10.1111/aor.13425.
23. Fábio F.F. Garrudo; Caitlyn A. Chapman; Pauline R. Hoffman; Ranodhi W. Udangawa; João C. Silva; Paiyz E. Mikael; Carlos A.V. Rodrigues; Joaquim M.S. Cabral; Jorge M.F. Morgado; Frederico C. Ferreira; et al. Robert J. Linhardt Polyaniline-polycaprolactone blended nanofibers for neural cell culture. *European Polymer Journal* **2019**, *117*, 28-37, 10.1016/j.eurpolymj.2019.04.048.
24. Azin Ghasemi; Rana Imani; Maryam Yousefzadeh; Shahin Bonakdar; Atefeh Solouk; Hossein Fakhrzadeh; Studying the Potential Application of Electrospun Polyethylene Terephthalate/Graphene Oxide Nanofibers as Electroconductive Cardiac Patch. *Macromolecular Materials and Engineering* **2019**, *304*, 1900187, 10.1002/mame.201900187.
25. Brian W. Walker; Roberto Portillo Lara; Chu Hsiang Yu; Ehsan Shirzaei Sani; William Kimball; Shannon Joyce; Nasim Annabi; Engineering a naturally-derived adhesive and conductive cardiopatch.. *Biomaterials* **2019**, *207*, 89-101, 10.1016/j.biomaterials.2019.03.015.
26. Neda Almasi; Simzar Hosseinzadeh; Shadie Hatamie; Gholamreza Taheri Sangsari; Stable conductive and biocompatible scaffold development using graphene oxide (GO) doped polyaniline (PANI). *International Journal of Polymeric Materials and Polymeric Biomaterials* **2019**, *no*, 1-11, 10.1080/00914037.2019.1628028.
27. Saeid Bahrami; Atefeh Solouk; Hamid Mirzadeh; Alexander M. Seifalian; Electroconductive polyurethane/graphene nanocomposite for biomedical applications. *Composites Part B: Engineering* **2019**, *168*, 421-431, 10.1016/j.compositesb.2019.03.044.
28. Hilary Stone; Shigang Lin; Kibret Mequanint; Preparation and characterization of electrospun rGO-poly(ester amide) conductive scaffolds.. *Materials Science and Engineering: C* **2018**, *98*,

- 324-332, 10.1016/j.msec.2018.12.122.
29. Nien-Chen Tsai; Jia-Wei She; Jhih-Guang Wu; Peilin Chen; Yu-Sheng Hsiao; Jiashing Yu; Poly(3,4-ethylenedioxythiophene) Polymer Composite Bioelectrodes with Designed Chemical and Topographical Cues to Manipulate the Behavior of PC12 Neuronal Cells. *Advanced Materials Interfaces* **2019**, 6, 1801576, 10.1002/admi.201801576.
 30. Junyan Yao; Yifu Chen; Wudan Li; Xiao Chen; Xiaodong Fan; Fabrication and characterization of electrospun PLLA/PANI/TSA fibers. *RSC Advances* **2019**, 9, 5610-5619, 10.1039/c8ra10495f.
 31. Atike Ince Yardimci; Hande Aypek; Ozgur Ozturk; Selahattin Yilmaz; Engin Ozcivici; Gulistan Mese; Yusuf Selamat; CNT Incorporated Polyacrylonitrile/Polypyrrole Nanofibers as Keratinocytes Scaffold. *Journal of Biomimetics, Biomaterials and Biomedical Engineering* **2019**, 41, 69-81, 10.4028/www.scientific.net/jbbbe.41.69.
 32. Yumei Li; Rui Zhao; Xiang Li; Chuying Wang; Huiwei Bao; Shudan Wang; Jing Fang; Jinqiu Huang; Ce Wang; Blood-compatible Polyaniline Coated Electrospun Polyurethane Fiber Scaffolds for Enhanced Adhesion and Proliferation of Human Umbilical Vein Endothelial Cells. *Fibers and Polymers* **2019**, 20, 250-260, 10.1007/s12221-019-8735-0.
 33. Irén Juhász Junger; Daria Wehlage; Robin Böttjer; Timo Grothe; László Juhász; Carsten Grassmann; Tomasz Blachowicz; Andrea Ehrmann; Dye-Sensitized Solar Cells with Electrospun Nanofiber Mat-Based Counter Electrodes. *Materials* **2018**, 11, 1604, 10.3390/ma11091604.
 34. László Juhász; Irén Juhász Junger; Spectral Analysis and Parameter Identification of Textile-Based Dye-Sensitized Solar Cells. *Materials* **2018**, 11, 1623, 10.3390/ma11091623.
 35. Sophia Kohn; Daria Wehlage; Irén Juhász Junger; Andrea Ehrmann; Kohn; Juhász Junger; Electrospinning a Dye-Sensitized Solar Cell. *Catalysts* **2019**, 9, 975, 10.3390/catal9120975.
 36. Sanaz Eslah; Mahdi Nouri; Synthesis and Characterization of Tungsten Trioxide/Polyaniline/Polyacrylonitrile Composite Nanofibers for Application as a Counter Electrode of DSSCs. *Russian Journal of Electrochemistry* **2019**, 55, 291-304, 10.1134/s1023193519030054.
 37. Dai-Hua Jiang; Ping-Chun Tsai; Chi Ching Kuo; Fu-Cheng Jhuang; Hao-Cheng Guo; Shih-Pin Chen; Ying-Chih Liao; Toshifumi Satoh; Shih-Huang Tung; Facile Preparation of Cu/Ag Core/Shell Electrospun Nanofibers as Highly Stable and Flexible Transparent Conductive Electrodes for Optoelectronic Devices. *ACS Applied Materials & Interfaces* **2019**, 11, 10118-10127, 10.1021/acsami.8b18366.
 38. Jianhang Sun; Jiangnan Liu; Han Chen; Xu Han; Yun Wu; Jin He; Ce Han; Guocheng Yang; Yuping Shan; Strongly coupled Mo₂C and Ni nanoparticles with in-situ formed interfaces encapsulated by porous carbon nanofibers for efficient hydrogen evolution reaction under alkaline

- conditions. *Journal of Colloid and Interface Science* **2020**, 558, 100-105, 10.1016/j.jcis.2019.09.102.
39. Meixuan Li; Yun Zhu; Na Song; Ce Wang; Xiaofeng Lu; Fabrication of Pt nanoparticles on nitrogen-doped carbon/Ni nanofibers for improved hydrogen evolution activity. *Journal of Colloid and Interface Science* **2018**, 514, 199-207, 10.1016/j.jcis.2017.12.028.
 40. Zexia Zhang; Yuanxi Wang; Xiangxing Leng; Vincent H. Crespi; Feiyu Kang; Ruitao Lv; Controllable Edge Exposure of MoS₂ for Efficient Hydrogen Evolution with High Current Density. *ACS Applied Energy Materials* **2018**, 1, 1268-1275, 10.1021/acsaem.8b00010.
 41. Youngwoo Rheem; Yosep Han; Kyu-Hwan Lee; Sung-Mook Choi; Nosang Myung; Synthesis of hierarchical MoO₂/MoS₂ nanofibers for electrocatalytic hydrogen evolution. *Nanotechnology* **2017**, 28, 105605, 10.1088/1361-6528/aa5c2f.
 42. Chengbin Liu; Longlu Wang; Yanhong Tang; Shenglian Luo; Yutang Liu; Shuqu Zhang; Yunxiong Zeng; Yuzi Xu; Vertical single or few-layer MoS₂ nanosheets rooting into TiO₂ nanofibers for highly efficient photocatalytic hydrogen evolution. *Applied Catalysis B: Environmental* **2015**, 164, 1-9, 10.1016/j.apcatb.2014.08.046.
 43. Hyerim Lee; Yeomin Kim; Areum Yu; Dasol Jin; Ara Jo; Youngmi Lee; Myung Hwa Kim; Chongmok Lee; An Efficient Electrochemical Sensor Driven by Hierarchical Hetero-Nanostructures Consisting of RuO₂ Nanorods on WO₃ Nanofibers for Detecting Biologically Relevant Molecules.. *Sensors* **2019**, 19, 3295, 10.3390/s19153295.
 44. Okoroike C. Ozoemena; Leshweni J. Shai; Tobile Maphumulo; Kenneth I. Ozoemena; Electrochemical Sensing of Dopamine Using Onion-like Carbons and Their Carbon Nanofiber Composites. *Electrocatalysis* **2019**, 10, 381-391, 10.1007/s12678-019-00520-x.
 45. Joshua Avossa; Roberto Paolesse; Corrado Di Natale; Emiliano Zampetti; Giovanni Bertoni; Fabrizio De Cesare; Giuseppe Scarascia-Mugnozza; Antonella Macagnano; Electrospinning of Polystyrene/Polyhydroxybutyrate Nanofibers Doped with Porphyrin and Graphene for Chemiresistor Gas Sensors. *Nanomaterials* **2019**, 9, 280, 10.3390/nano9020280.
 46. Ahmed Shaker; Ahmed Hassanin; Nagih Shaalan; Mohsen Hassan; Ahmed Abdelmoneim; Micropatterned flexible strain gauge sensor based on wet electrospun polyurethane/PEDOT:PSS nanofibers. *Smart Materials and Structures* **2019**, 28, 075029, 10.1088/1361-665x/ab20a2.
 47. Kai Yang; Fuxing Yin; Dan Xia; Huifen Peng; Jinzheng Yang; Wenjing Yuan; A highly flexible and multifunctional strain sensor based on a network-structured MXene/polyurethane mat with ultra-high sensitivity and a broad sensing range. *Nanoscale* **2019**, 11, 9949-9957, 10.1039/c9nr00488b.
 48. Nazanin Khalili; Marco Chu; Hani E Naguib; Solvent-assisted electrospun fibers with ultrahigh stretchability and strain sensing capabilities. *Smart Materials and Structures* **2019**, 28, 055018, 1

0.1088/1361-665x/ab0d4d.

49. Miaoning Ren; Yujie Zhou; Yan Wang; Guoqiang Zheng; Kun Dai; Chuntai Liu; Changyu Shen; Highly stretchable and durable strain sensor based on carbon nanotubes decorated thermoplastic polyurethane fibrous network with aligned wave-like structure. *Chemical Engineering Journal* **2019**, 360, 762-777, 10.1016/j.cej.2018.12.025.
50. Nan Nan; Jianxin He; Xiaolu You; Xianqiang Sun; Yuman Zhou; Kun Qi; Weili Shao; Fan Liu; Yanyan Chu; Bin Ding; et al. A Stretchable, Highly Sensitive, and Multimodal Mechanical Fabric Sensor Based on Electrospun Conductive Nanofiber Yarn for Wearable Electronics. *Advanced Materials Technologies* **2018**, 4, 1088338, 10.1002/admt.201800338.
51. Madis Harjo; Zane Zondaka; Kaur Leemets; Martin Järvekülg; Tarmo Tamm; Rudolf Kiefer; Polypyrrole-coated fiber-scaffolds: Concurrent linear actuation and sensing. *Journal of Applied Polymer Science* **2019**, 137, no, 10.1002/app.48533.
52. Jéssyka Carolina Bittencourt; Bruno Henrique De Santana Gois; Vinicius Jessé Rodrigues De Oliveira; Deuber Lincon Da Silva Agostini; Clarissa De Almeida Olivati; Gas sensor for ammonia detection based on poly(vinyl alcohol) and polyaniline electrospun. *Journal of Applied Polymer Science* **2018**, 136, 47288., 10.1002/app.47288.
53. Wang, J.; Naguib, H.E.; Bazylak, A. Electrospun porous conductive polymer membranes. In Proceedings of the SPIE—The International Society for Optical Engineering, San Diego, CA, USA, 11–15 March 2012.
54. Derya Akcoren; Merih Zeynep Avci; Zeliha Guler Gokce; Timucin Balkan; A. Sezai Sarac; Fabrication and characterization of poly(butyl acrylate-co-methyl methacrylate)-polypyrrole nanofibers. *Polymer Bulletin* **2017**, 75, 1607-1617, 10.1007/s00289-017-2110-3.
55. Sita Shrestha; Bishnu Kumar Shrestha; Joshua Lee; Oh. Kwang Joong; Beom-Su Kim; Chan Hee Park; Cheol Sang Kim; A conducting neural interface of polyurethane/silk-functionalized multiwall carbon nanotubes with enhanced mechanical strength for neuroregeneration.. *Materials Science and Engineering: C* **2019**, 102, 511-523, 10.1016/j.msec.2019.04.053.
56. Wangcheng Liu; Jinwen Zhang; Hang Liu; Conductive Bicomponent Fibers Containing Polyaniline Produced via Side-by-Side Electrospinning.. *Polymers* **2019**, 11, 954, 10.3390/polym11060954.
57. Yao Li; Aleksander Góra; Franklin Anariba; Avinash Baji; Enhanced tensile strength and electrical conductivity of electrospun polyacrylonitrile Yarns via post-treatment. *Polymer Composites* **2018**, 40, 1702-1707, 10.1002/pc.24920.
58. Nasim Shokraei; Shiva Asadpour; Shabnam Shokraei; Mehrdad Nasrollahzadeh Sabet; Reza Faridi-Majidi; Hossein Ghanbari; Development of electrically conductive hybrid nanofibers based on CNT-polyurethane nanocomposite for cardiac tissue engineering.. *Microscopy Research and Technique* **2019**, 82, 1316-1325, 10.1002/jemt.23282.

59. Yaxuan Xu; Zhongbing Huang; Ximing Pu; Guangfu Yin; Jiankai Zhang; Fabrication of Chitosan/Polypyrrole-coated poly(L-lactic acid)/Polycaprolactone aligned fibre films for enhancement of neural cell compatibility and neurite growth.. *Cell Proliferation* **2019**, 52, e12588, 10.1111/cpr.12588.
60. Yongqiang Guo; Lulu Pan; Xutong Yang; Kunpeng Ruan; Yixin Han; Jie Kong; Junwei Gu; Simultaneous improvement of thermal conductivities and electromagnetic interference shielding performances in polystyrene composites via constructing interconnection oriented networks based on electrospinning technology. *Composites Part A: Applied Science and Manufacturing* **2019**, 124, 105484., 10.1016/j.compositesa.2019.105484.
61. Tianya Li; Yulong Xu; Kejian Wang; Jinghui Song; Hengwei Hu; Han Liu; Yueqi Liu; Yong Liu; Jing Wu; Haohong Pi; et al.Seeram Ramakrishna Preparation and performance of hydrophobic and conductive silica composite fiber membrane. *Journal of Materials Science* **2019**, 55, 191-202, 10.1007/s10853-019-04015-4.
62. Alexis Laforgue; Lucie Robitaille; Production of Conductive PEDOT Nanofibers by the Combination of Electrospinning and Vapor-Phase Polymerization. *Macromolecules* **2010**, 43, 4194-4200, 10.1021/ma9027678.
63. Seyed Vahid Ebadi; Dariush Semnani; Hossein Fashandi; Behzad Rezaei; Synthesis and characterization of a novel polyurethane/polypyrrole-p-toluenesulfonate (PU/PPy-pTS) electroactive nanofibrous bending actuator. *Polymers for Advanced Technologies* **2019**, 30, 2261-2274, 10.1002/pat.4655.
64. Kiran Yadav; Ratyakshi Nain; Manjeet Jassal; Ashwini K. Agrawal; Free standing flexible conductive PVA nanoweb with well aligned silver nanowires. *Composites Science and Technology* **2019**, 182, 107766, 10.1016/j.compscitech.2019.107766.
65. Arsalan Ahmed; Yunming Jia; Yi Huang; Nazakat Ali Khoso; Hridam Deb; Qinguo Fan; Jianzhong Shao; Preparation of PVDF-TrFE based electrospun nanofibers decorated with PEDOT-CNT/rGO composites for piezo-electric pressure sensor. *Journal of Materials Science: Materials in Electronics* **2019**, 30, 14007-14021, 10.1007/s10854-019-01751-w.

Retrieved from <https://encyclopedia.pub/entry/history/show/6690>