

Polymer-Based Thermal Management Material

Subjects: **Polymer Science**

Contributor: Aijie Ma

The thermally conductive polymer is usually categorized into the intrinsic thermally conductive polymers and the thermally conductive polymer composites.

thermal management material

thermal conductivity

1. Intrinsic Thermally Conductive Polymers

On the basis of the preparation process, the thermally conductive polymer is usually categorized into the intrinsic thermally conductive polymers and the thermally conductive polymer composites ^[1]. The thermal conductivity of solid material is mainly determined by the thermal conduction of phonons (energy quanta of lattice vibrations) and free electrons ^[2]. For polymers, regarded as thermal insulators, the thermal conductivity of polymers is dominated by the contribution of phonons, while in metals, the contribution from electrons is much greater than that of phonons ^{[3][4]}. According to Debye's assumptions, the thermal conductivity (K) of polymers could be expressed as Equation:

$$K = CP\nu l \div 3$$

where C_p is the specific heat capacity per unit volume, ν is the phonon velocity and l represents the phonon mean free path. For bulk polymers, the thermal conductivity is extremely low ($<0.5 \text{ Wm}^{-1}\text{K}^{-1}$) ^[5]. The polymer chains of bulk polymer are in a twisted and random orientation state, and there are a great number of crystal–amorphous interfaces, chain ends, defects and voids, all of which result in strong phonon scattering thus extremely low thermal conductivity. Conversely, by molecular dynamics simulations, Henry and Chen calculated that the thermal conductivity of single polyethylene (PE) chains is up to $350 \text{ Wm}^{-1}\text{K}^{-1}$ ^[6]. For most polymers, ν and C_p are almost the same as those of single chain, thus the difference of thermal conductivity between single-chain and bulk polymer is caused by the value of l ^[7]. Therefore, in the process of polymerization and processing, transforming the structure of polymer chains into regular arrangement in a certain direction is the key to obtain intrinsic thermally conductive polymers. Recently, many studies have demonstrated that changing the molecular chain structure, increasing the crystallinity, transforming the crystal form and enhancing orientation of molecular chains are effective strategies to improve the thermal conductivity of the intrinsic polymers ^[8] (Figure 1).

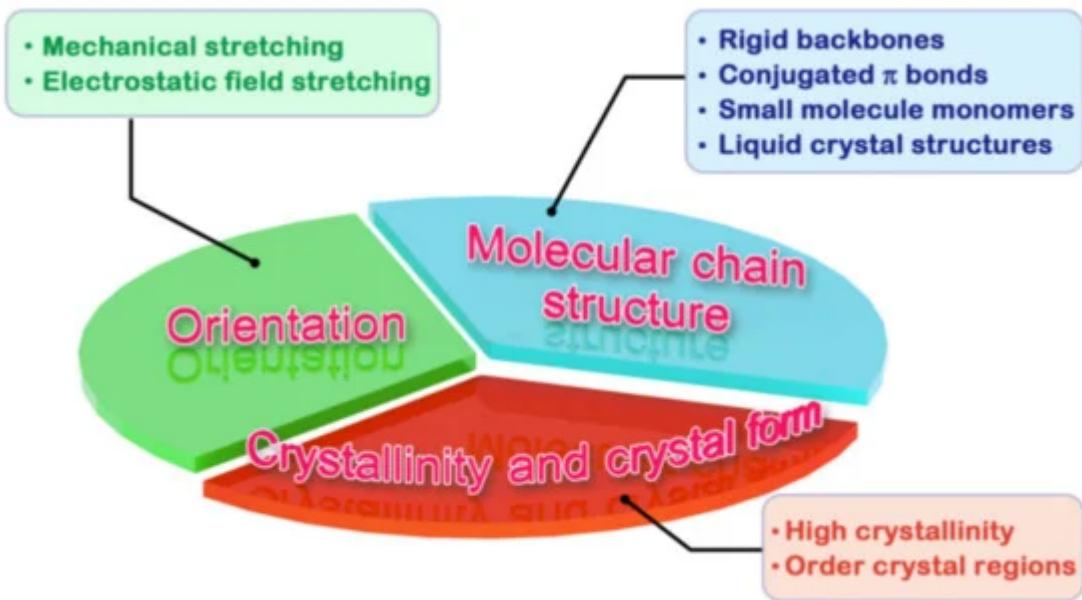


Figure 1. Thermal conductivity of intrinsic thermally conductive polymers depends on various factors that need to be considered.

2. Molecular Chain Structure

Polymers with rigid backbones have higher thermal conductivity, such as polyphenylene sulfide (PPS)^[9], because the rigid backbone can inhibit the rotation of polymer chains and ameliorate the transmission of phonons. Conjugated π -bonded polymers also exhibit higher thermal conductivity, such as polyacetylene, polyaniline, polypyrrole, polythiophene, etc. This is due to the phonon heat conduction mechanism as well as the electron heat conduction mechanism. Zheng et al.^[10] synthesized copolymers of 3-alkylthiophene and 3-alkoxythiophene with different p- π conjugation degree by oxidative polymerization. The results of laser measurement and molecular dynamics simulation show that the copolymers with high p- π conjugation degree have thermal conductivity as high as $0.374 \text{ Wm}^{-1}\text{K}^{-1}$. In addition, the introduction of small molecule monomers, liquid crystal structures or other regular structures in the synthesis of polymers can improve the microscopic order of the polymers, thus enhancing thermal conductivity^[11]. As shown in **Figure 2a**, Song et al.^[12] reported that the mesogenic epoxy resin maintains a high thermal conductivity of $0.33 \text{ Wm}^{-1}\text{K}^{-1}$, which is 1.7 times higher than that of amorphous epoxy resin, and the mesogenic epoxy resin with spherulite structure have a higher thermal conductivity of $1.16 \text{ Wm}^{-1}\text{K}^{-1}$. Recently, Ruan et al.^[13] synthesized liquid crystalline polyimide (LC-PI) films using phthalimide groups as the mesomorphic units. The obtained LC-PI films with microscopically ordered molecular chains exhibit high thermal conductivity of $2.11 \text{ Wm}^{-1}\text{K}^{-1}$ (in-plane) and $0.32 \text{ Wm}^{-1}\text{K}^{-1}$ (through-plane).

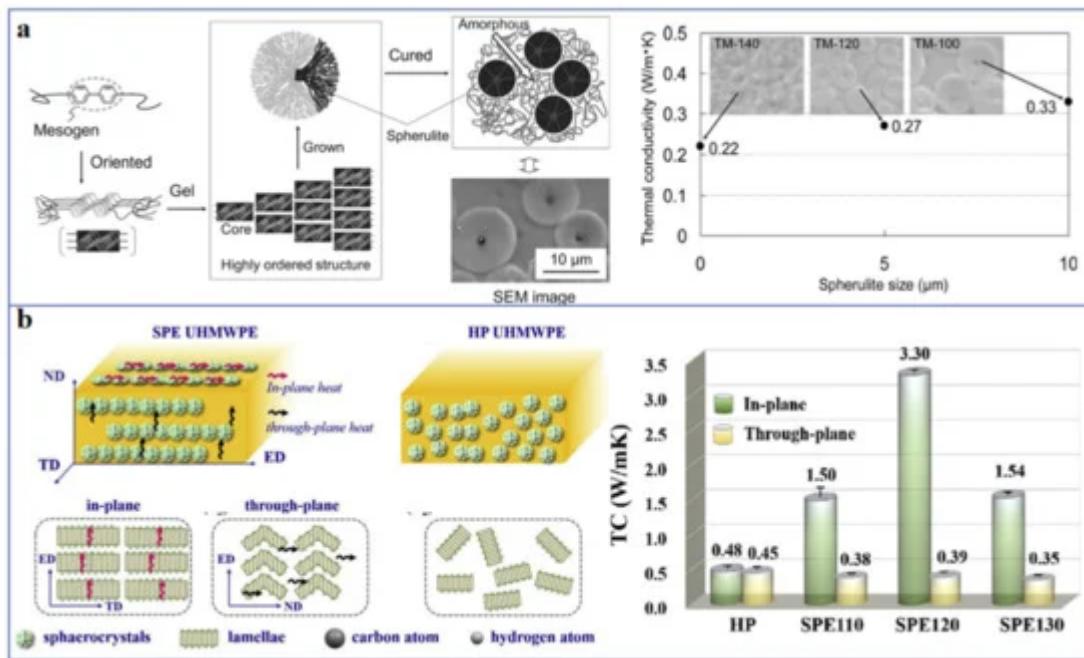


Figure 2. Schematics of the influence of (a) molecular chain structure ^[12] (Copyright (2012) with permission from Elsevier Ltd.) and (b) crystal morphology ^[14] on thermal conductivity (Copyright (2019) with permission from Elsevier Ltd.).

3. Crystallinity and Crystal Morphology

Crystallization can increase the degree of structural order in polymer, so the thermal conductivity of crystalline polymers is generally higher than that of amorphous polymers, and the thermal conductivity of crystalline polymers increases with the increase of crystallinity ^{[15][16]}. Bai et al. ^[17] discussed the effect of crystallinity degree of poly-l-lactide (PLLA) on thermal conductivity. The results show that the thermal conductivity of PLLA increases from 0.16 $\text{Wm}^{-1}\text{K}^{-1}$ (amorphous PLLA) to 0.2 $\text{Wm}^{-1}\text{K}^{-1}$ when the crystallinity is 56%. Because the crystallinity of most polymers is less than 100%, there will inevitably be an interface between crystal and amorphous region, which will lead to phonon scattering and reduce the thermal conductivity. For instance, Huang et al. ^[14] reported that the ultrahigh molecular weight polyethylene (UHMWPE) has high thermal conductivity of 3.30 $\text{Wm}^{-1}\text{K}^{-1}$, which is due to the reduction of interface between crystals and amorphous regions through the formation of cylindrical crystals and highly oriented lamellae (Figure 2b). In addition, some studies show that the crystal morphology also has an important influence on the thermal conductivity of polymer. For example, the thermal conductivity of high-density polyethylene (HDPE) and UHMWPE with extended-chain crystals is higher than that of folded-chain lamella crystals ^[16].

4. Orientation of Molecular Chains

As mentioned above, the main factor causing the low thermal conductivity of the polymer is the random arrangement of the polymer molecular chains, because it is easier to conduct heat along the molecular chains

rather than lateral direction. Therefore, the anisotropic thermal conductivity (especially the enhanced thermal conductivity along the stretching direction) can be achieved by aligning polymer molecular chains along a specific direction by mechanical stretching. So far, many experiments have studied the effect of orientation on the thermal conductivity of polymers, including crystalline and amorphous polymers [9][18][19].

For crystalline polymers, many studies have focused on polyethylene (PE). For example, Choy et al. [20] reported that when the drawing ratio is in the range of 1–25, the thermal conductivity of HDPE parallel to the stretching direction is much higher than that of HDPE perpendicular to the stretching direction in the temperature range of 120–320 K. To be specific, when the drawing ratio is 25, the thermal conductivity of HDPE parallel to the drawing direction is up to $8.5 \text{ W}^{-1}\text{mK}^{-1}$ (120 K) and $14 \text{ Wm}^{-1}\text{K}^{-1}$ (320 K). Choy et al. [21] further studied the effect of different drawing ratios (in the range of 1–350) on the thermal conductivity of PE, and the ultra-drawing PE fibers with the drawing ratio of 350 has a high thermal conductivity of $41.8 \text{ Wm}^{-1}\text{K}^{-1}$ in the drawing direction. This can be explained by the fact that when the drawing ratio increases, the crystal lamellae are broken into small crystal blocks and then rearranged to form microfibers; after further stretching, the microfibers are deformed into ordered long extended-chain crystals or even needle-like crystals. Shen et al. [22] also fabricated a series of ultra-stretched PE nanofibers, whose drawing ratio (60–800) is higher than that of Choy [21], and the highest thermal conductivity reaches $104 \text{ Wm}^{-1}\text{K}^{-1}$, which is almost close to the properties of PE single crystals.

References

1. Yang, X.; Liang, C.; Ma, T.; Guo, Y.; Kong, J.; Gu, J.; Chen, M.; Zhu, J. A review on thermally conductive polymeric composites: Classification, measurement, model and equations, mechanism and fabrication methods. *Adv. Compos. Hybrid Mater.* 2018, 1, 207–230.
2. Zhang, Y.; Heo, Y.-J.; Son, Y.-R.; In, I.; An, K.-H.; Kim, B.-J.; Park, S.-J. Recent advanced thermal interfacial materials: A review of conducting mechanisms and parameters of carbon materials. *Carbon* 2019, 142, 445–460.
3. An, D.; Cheng, S.; Zhang, Z.; Jiang, C.; Fang, H.; Li, J.; Liu, Y.; Wong, C.-P. A polymer-based thermal management material with enhanced thermal conductivity by introducing three-dimensional networks and covalent bond connections. *Carbon* 2019, 155, 258–267.
4. Ma, H.; Gao, B.; Wang, M.; Yuan, Z.; Shen, J.; Zhao, J.; Feng, Y. Strategies for enhancing thermal conductivity of polymer-based thermal interface materials: A review. *J. Mater. Sci.* 2020, 56, 1064–1086.
5. Han, Z.; Fina, A. Thermal conductivity of carbon nanotubes and their polymer nanocomposites: A review. *Prog. Polym. Sci.* 2011, 36, 914–944.
6. Henry, A.; Chen, G. High thermal conductivity of single polyethylene chains using molecular dynamics simulations. *Phys. Rev. Lett.* 2008, 101, 235502.

7. Chen, H.; Ginzburg, V.V.; Yang, J.; Yang, Y.; Liu, W.; Huang, Y.; Du, L.; Chen, B. Thermal conductivity of polymer-based composites: Fundamentals and applications. *Prog. Polym. Sci.* 2016, 59, 41–85.
8. Xu, Y.; Wang, X.; Hao, Q. A mini review on thermally conductive polymers and polymer-based composites. *Compos. Commun.* 2021, 24, 100617.
9. Langer, L.; Billaud, D.; Issi, J.-P. Thermal conductivity of stretched and annealed poly (p-phenylene sulfide) films. *Solid State Commun.* 2003, 126, 353–357.
10. Zheng, H.; Wu, K.; Chen, W.; Nan, B.; Qu, Z.; Lu, M. High Intrinsic Thermal Conductivity of Polythiophene by Reducing Steric Hindrance and Enhancing p-π Conjugation. *Macromol. Chem. Phys.* 2021, 222, 2000418.
11. Harada, M.; Hamaura, N.; Ochi, M.; Agari, Y. Thermal conductivity of liquid crystalline epoxy/BN filler composites having ordered network structure. *Compos. Part B* 2013, 55, 306–313.
12. Song, S.-h.; Katagi, H.; Takezawa, Y. Study on high thermal conductivity of mesogenic epoxy resin with spherulite structure. *Polymer* 2012, 53, 4489–4492.
13. Ruan, K.; Guo, Y.; Gu, J. Liquid Crystalline Polyimide Films with High Intrinsic Thermal Conductivities and Robust Toughness. *Macromolecules* 2021, 54, 4934–4944.
14. Huang, Y.-F.; Wang, Z.-G.; Yu, W.-C.; Ren, Y.; Lei, J.; Xu, J.-Z.; Li, Z.-M. Achieving high thermal conductivity and mechanical reinforcement in ultrahigh molecular weight polyethylene bulk material. *Polymer* 2019, 180, 121760.
15. Liu, J.; Xu, Z.; Cheng, Z.; Xu, S.; Wang, X. Thermal Conductivity of Ultrahigh Molecular Weight Polyethylene Crystal: Defect Effect Uncovered by 0 K Limit Phonon Diffusion. *ACS Appl. Mater. Interfaces* 2015, 7, 27279–27288.
16. Yu, J.; Sundqvist, B.; Tonpheng, B.; Andersson, O. Thermal conductivity of highly crystallized polyethylene. *Polymer* 2014, 55, 195–200.
17. Bai, L.; Zhao, X.; Bao, R.-Y.; Liu, Z.-Y.; Yang, M.-B.; Yang, W. Effect of temperature, crystallinity and molecular chain orientation on the thermal conductivity of polymers: A case study of PLLA. *J. Mater. Sci.* 2018, 53, 10543–10553.
18. Zhong, Z.; Wingert, M.C.; Strzalka, J.; Wang, H.H.; Sun, T.; Wang, J.; Chen, R.; Jiang, Z. Structure-induced enhancement of thermal conductivities in electrospun polymer nanofibers. *Nanoscale* 2014, 6, 8283–8291.
19. Zhang, R.-C.; Huang, Z.; Sun, D.; Ji, D.; Zhong, M.; Zang, D.; Xu, J.-Z.; Wan, Y.; Lu, A. New insights into thermal conductivity of uniaxially stretched high density polyethylene films. *Polymer* 2018, 154, 42–47.

20. Choy, C.L.; Luk, W.H.; Chen, F.C. Thermal conductivity of highly oriented polyethylene. *Polymer* 1978, 19, 155–162.
21. Choy, C.L.; Wong, Y.W.; Yang, G.W.; Kanamoto, T. Elastic modulus and thermal conductivity of ultradrawn polyethylene. *J. Polym. Sci. Part B Polym. Phys.* 1999, 37, 3359–3367.
22. Shen, S.; Henry, A.; Tong, J.; Zheng, R.; Chen, G. Polyethylene nanofibres with very high thermal conductivities. *Nat. Nanotechnol.* 2010, 5, 251–255.

Retrieved from <https://encyclopedia.pub/entry/history/show/32898>