

# MOF-based adsorbents for atmospheric emission

Subjects: Others

Contributor: Domenico Caputo

This topic focuses on the use of metal–organic frameworks (MOFs) for adsorbing gas species that are known to weaken the thermal self-regulation capacities of Earth's atmosphere. A large section is dedicated to the adsorption of carbon dioxide, while another section is dedicated to the adsorption of other different gas typologies, whose emissions, for various reasons, represent a “wound” for Earth's atmosphere. High emphasis is given to MOFs that have moved enough ahead in their development process to be currently considered as potentially usable in “real-world” (i.e., out-of-lab) adsorption processes. As a result, there is strong evidence of a wide gap between laboratory results and the industrial implementation of MOF-based adsorbents. Indeed, when a MOF that performs well in a specific process is commercially available in large quantities, economic observations still make designers tend toward more traditional adsorbents. Moreover, there are cases in which a specific MOF remarkably outperforms the currently employed adsorbents, but it is not industrially produced, thus strongly limiting its possibilities in large-scale use. To overcome such limitations, it is hoped that the chemical industry will be able to provide more and more mass-produced MOFs at increasingly competitive costs in the future.

Keywords: metal-organic frameworks ; adsorption ; greenhouse gases ; atmospheric environment ; climate change

---

## 1. Introduction


Since its first historical traces, mankind has never had to face global challenges such as those happening in the contemporary age. Among them, climate change is the challenge nowadays considered to be the most threatening for the survival of the whole human race

[1]. Climate change is mainly dependent on the energy transport phenomena occurring between Earth and outer space. In turn, such energy transport phenomena are strongly related to the physicochemical status of Earth's atmosphere. After the Industrial Revolution took place from the second half of the 18th century to the first half of the 19th century, anthropic activities started to dramatically influence the “health” of the Earth's atmosphere. Therefore, the energy balance of our planet is being modified in such a way that its average temperature is abnormally increasing (global warming). This temperature increase is already causing anomalous climatic events, which are unprecedented in human history and recall prehistorical periods of planetary crisis such as Late Quaternary extinctions [2]. In order to try reverting global warming, immediate action must be taken to minimize anthropic emissions that modify the chemical composition of Earth's atmosphere. Among the unit operations of the process industry, adsorption has turned out to be the most efficient for separating gas mixtures in fractions or in pure components [3]. In other words, adsorption represents the cleanest way of capturing pollutants from end-of-process gas streams that are discharged into the atmosphere. When designing an adsorption system, one of the crucial choices concerns the type of adsorbent material that will be used in the packed beds. The materials mostly contemplated for adsorption processes are nanoporous materials [4], in particular, microporous materials (with pore sizes below 2 nm) and mesoporous materials (with pore sizes between 2 and 50 nm). During the last 15 years, microporous metal–organic frameworks (MOFs) have shown great potential for improving the performances of different industrially relevant, adsorption-based applications[5]. This review will focus on the use of MOFs for adsorbing gas species, which are known to weaken the thermal self-regulation capacities of Earth's atmosphere. Obviously, a large section will be dedicated to the adsorption of carbon dioxide, whose emissions are the main cause of the so-called greenhouse effect, while another section will be dedicated to the adsorption of other different gas typologies (e.g., fluorinated gases, volatile organic compounds, etc.) whose emissions, for various reasons, represent a “wound” for Earth's atmosphere. Nevertheless, the critical approach to the following literature survey was based on the search for the three main functionalities that an ideal adsorbent should always feature:

- i. High adsorption capacity toward the target adsorptive (e., the value of the adsorbed amount of substance observed in saturation conditions);
- ii. High selectivity toward the target adsorptive (e., the ability of the adsorbent to preferably adsorb one adsorptive when mixed with others);

iii. High regeneration capacity (e., the possibility of removing the adsorbate by means of simple and inexpensive methods, in order to use the same adsorbent for repeated adsorption cycles).

Moreover, high emphasis will be given to studies about MOFs that have moved ahead enough in their development process to be currently considered as potentially usable in “real-world” (i.e., out-of-lab) adsorption processes. The crystal structures of some of these MOFs, whose performances as adsorbents will be detailed in the next sections, are shown in Figure 1.

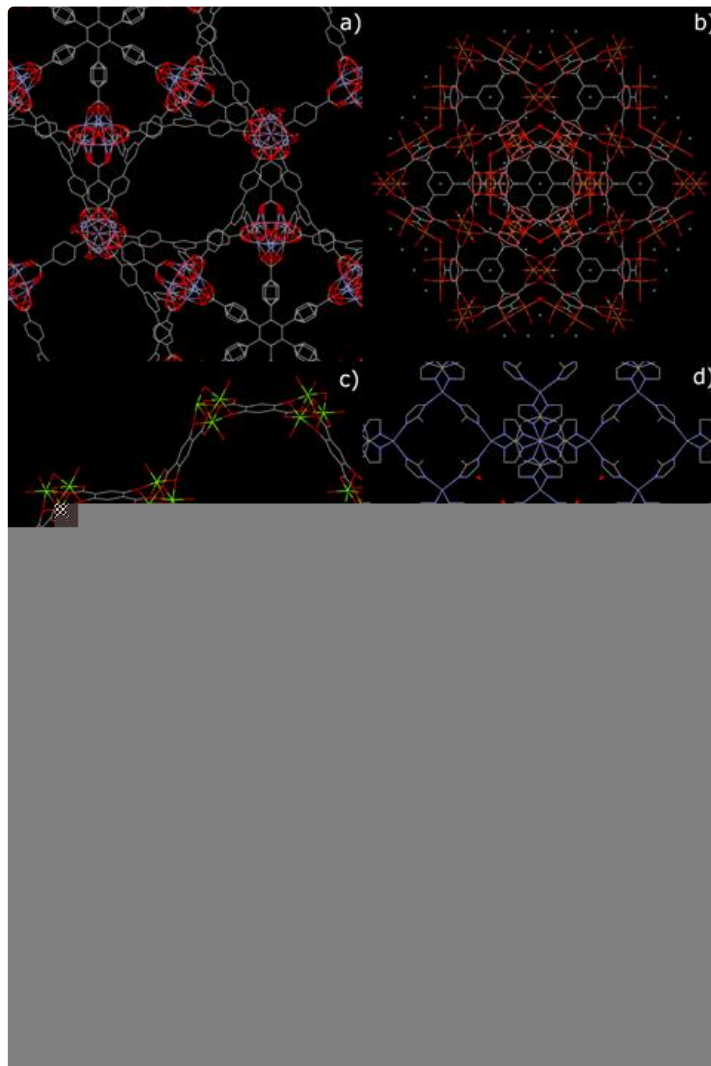

**Figure 1.** Crystal structures of some mass-produced metal–organic frameworks (MOFs): (a) MOF-177; (b) Cu-BTC; (c) Mg-MOF-74; (d) ZIF-8; (e) PCN-250 (Fe<sub>3</sub>); (f) UiO-66.

## 2. CO<sub>2</sub> adsorption on MOFs

Starting from the advent of the Industrial Revolution, anthropic activities caused an increase in carbon dioxide atmospheric concentration of more than 50%, *i.e.*, from about 260 ppm of pre-industrial era <sup>[6]</sup> the current 400 ppm (and more)<sup>[7]</sup>. Such anomalous change in the composition of Earth’s atmosphere is significantly reducing the fraction of absorbed solar radiant energy that the planet gives back to outer space. This phenomenon, known as greenhouse effect <sup>[8]</sup>, is the main cause of the abnormal planetary temperature rise registered during the last two centuries. Anthropic CO<sub>2</sub> emissions mainly come from three sources:

- i. transportation, through combustion of fossil fuels;
- ii. electricity production, (again) through combustion of fossil fuels;
- iii. industry, through reforming of fossil fuels, gaseous byproducts of industrial steelmaking and cement industry, etc.

As particularly regards the last two scenarios, the implementation of adsorption columns downstream of electricity production and industrial plants can provide a drastic reduction of CO<sub>2</sub> emissions <sup>[9][20][21][22][23][24][25][26][27][28][29][30][31][32][33][34][35][36][37][38][39][40][41][42]</sup>. Up to the end of the last century, zeolites were considered the best option among nanoporous adsorbents for CO<sub>2</sub> capture and they are still considered the benchmark in terms of benefit-cost ratio <sup>[10]</sup>, also

because zeolites can be synthesized starting from several waste materials <sup>[11]</sup>. In the last two decades, a lot of efforts were focused in studying the CO<sub>2</sub> adsorption properties of functionalized mesoporous silicates <sup>[12][13][14][15][16]</sup>. Eventually, in the last 15 years, there has been an exponential development of studies about the CO<sub>2</sub> adsorption properties of MOFs. Readers who are interested only in this specific topic are invited to also read a recent review by Ghanbari *et al.* <sup>[17]</sup>. With respect to the latter paper, rather than focusing on the correlation between MOF structures and CO<sub>2</sub> adsorption performances, this section of the present review will give emphasis on the actual suitability of MOFs to be used in industrial CO<sub>2</sub> adsorption processes. In particular, potential applications in packed bed adsorption columns will be taken into account, whereas membrane-based separation needs specific treatises <sup>[18]</sup>. An overview of the recent (limited to the last decade) literature about this subject is reported in Table 1 <sup>[19][20][21][22][23][24][25][26][27][28][29][30][31][32][33][34][35][36][37][38][39][40][41][42][43][44][45][46][47][48][49][50][51][52][53][54][55][56][57][58][59][60][61][62][63][64][65][66][67][68][69][70][71][72][73][74][75][76][77]</sup>

**Table 1.** MOFs potentially suitable for CO<sub>2</sub> adsorption

MOF type	CO <sub>2</sub> adsorption capacity, <sup>1</sup> mol/kg (reported working conditions, <i>T</i> and <i>p</i> ) <sup>2</sup>	Reference
MOF-177	9.02 (298 K, 1400 kPa)	[19]
	1.00 (298 K, 100 kPa)	[23]
	0.93 (293 K, 100 kPa)	[39]
Ionic liquid – functionalized MOF-177	1.14 (303 K, 100 kPa)	[24]
	7.00 (283 K, 100 kPa)	[26]
	14.00 (303 K, 4000 kPa)	[28]
Cu-BTC	8.07 (303 K, 1000 kPa)	[29]
	11.70 (297 K, 1500 kPa)	[30]
	1.70 (303 K, 15 kPa)	[32]
Li – doped Cu-BTC	4.85 (298 K, 100 kPa)	[33]
	8.61 (298 K, 100 kPa)	[37]
	9.02 (293 K, 100 kPa)	[39]
Mg-MOF-74	15.00 (313 K, 3500 kPa)	[40]
	14.80 (303 K, 3000 kPa)	[41]
	4.98 (298 K, 100 kPa)	[44]
Mg-MOF-74 – polystyrene composite	6.06 (breakthrough, CO <sub>2</sub> /N <sub>2</sub> mixture, [CO <sub>2</sub> ] = 15 mol%, 333 K)	[45]
	6.11 (298 K, 100 kPa)	[46]
Tetraethylenepentamine – functionalized Mg-MOF-74		

Ethylenediamine – functionalized Mg-MOF-74	5.42 (298 K, 100 kPa)	[47]
ZIF-8	8.60 (303 K, 4000 kPa)	[48]
	9.10 (303 K, 4500 kPa)	[50]
Ammonia – functionalized ZIF-8	7.50 (298 K, 3000 kPa)	[51]
Ethylenediamine – functionalized ZIF-8	9.85 (298 K, 2500 kPa)	[52]
Tetraethylenepentamine – functionalized ZIF-8	2.18 – 3.19, depending on the amine content (318 K, 500 kPa)	[53]
3-amino-1,2,4-triazole – functionalized ZIF-8	2.51 (308 K, 200 kPa)	[55]
2-nitrobenzimidazole – functionalized ZIF-8	3.39 (273 K, 120 kPa)	[56]
Thermally annealed ZIF-8	3.00 (298 K, 250 kPa)	[57]
Li – doped polyoxometalate – ZIF-8 composite	16.00 (298 K, 1000 kPa)	[58]
Ionic liquid – functionalized ZIF-8	0.83 (303 K, 20 kPa)	[59]
PCN-250 (Fe <sub>3</sub> )	5.24 (breakthrough, CO <sub>2</sub> /N <sub>2</sub> mixture, [CO <sub>2</sub> ] = 15 vol%, 303 K)	[63]
	3.02 (298 K, 100 kPa)	[64]
	7.65 (303 K, 6000 kPa)	[65]
UiO-66	7.29 (298 K, 3000 kPa)	[66]
	1.48 (303 K, 100 kPa)	[67]
	4.34 (298 K, 2000 kPa)	[68]
Ti – exchanged UiO-66	4.37 (273 K, 120 kPa)	[72]
Adipic acid – functionalized UiO-66	3.76 (273 K, 100 kPa)	[73]
Ethanolamine – functionalized UiO-66	1.70 (298 K, 100 kPa)	[74]
Polyethylenimine – functionalized UiO-66	3.32 (298 K, 100 kPa)	[75]
Tetraethylenepentamine – functionalized UiO-66	3.70 (breakthrough, CO <sub>2</sub> /He mixture, [CO <sub>2</sub> ] = 10 vol%, 348 K, 100 kPa)	[76]

<sup>1</sup> Where not explicitly reported in the cited papers, CO<sub>2</sub> adsorption capacity values were extracted from plots using reverse engineering software.

<sup>2</sup> Where not explicitly reported, working conditions imply the collection of pure CO<sub>2</sub> adsorption isotherms.

A crucial, still overlooked aspect regards the need of shaped adsorbents for packing industrial scale beds, whereas all the examined materials are initially produced in powder form. Actually, commercial MOF providers offer powder shaping as an additional service [78], thus relieving the end user from this laborious task. Anyway, in order to be of any practical use inside adsorption columns, MOF powders need to be processed by means of classical methods such as granulation and pelletization [79]. In both the latter cases, adsorbent shaping comes with a cost, *i.e.*, it negatively affects the structural / textural properties of MOFs. The techniques used for shaping MOFs thus demand further research in order to optimize such manufacturing process [80][81][82]. The most detrimental side effects that must be still minimized are the collapse of the adsorbent crystalline lattice, the reduced access to its pore structure and the diffusion limitations of shaped bodies due to non-optimal void fractions between primary powders [83].

A last, even more crucial issue about the suitability of using MOFs in actual industrial CO<sub>2</sub> adsorption processes regards the comparison between the costs and the benefits that such a technological shift would bring along. Unfortunately, current analyses available in literature seem to point out that, despite their declared performance superiority, MOFs cannot compare to much cheaper traditional adsorbents. As an example (more systematic than others already cited), Danaci *et al.* assessed 22 different MOFs (some of which are among the ones listed in Table 1) against specific performance constraints and cost in CO<sub>2</sub> capture from flue gas using PVSA [84]. At the end of such a significant screening, the MOF that showed the best performance and lowest cost was a still-commercially-unavailable one (*i.e.*, UTSA-16), whose performance was in line with a much cheaper 13X zeolite anyway. It is hoped that studies like the latter one provide specific directions for material scientists to design MOF adsorbents with more focus on actual process needs than on the discovery of new structures *per se*.

### 3. MOFs for other adsorption processes significant for the atmospheric environment

As outlined in Section 1, in addition to CO<sub>2</sub>, there are other greenhouse gases and other gas typologies whose emissions, for various reasons, represent a significant “wound” for Earth’s atmosphere. Also in these cases, adsorption represents the cleanest way for capturing such pollutants from end-of-process gas streams, and MOFs could be considered a valid choice as materials for adsorption column packing.

#### 3.1. Adsorption of sulfur and nitrogen oxides

When emitted into the atmosphere, sulfur and nitrogen oxides (namely, SO<sub>x</sub> and NO<sub>x</sub>) contribute to ground-level ozone formation and are responsible for eutrophication, reduction in water quality and, eventually, species richness. They are also associated with adverse effects on human health as high concentrations cause respiratory illnesses. Both NO<sub>x</sub> and SO<sub>x</sub> are combustion products that are emitted into the atmosphere within flue gas. Indeed, most anthropogenic SO<sub>x</sub> and NO<sub>x</sub> emissions emerge from the combustion of coal and heavy oil. Moreover, other industrial processes are also specifically responsible for significant SO<sub>2</sub> emissions [85][86].

During the last 15 years, the scientific community has shown a growing interest in the attempt to capture industrially originating SO<sub>x</sub> and NO<sub>x</sub> before their emission into the atmosphere. MOFs, due to their great sorption capacities and their selectivity in capturing a large number of toxic and pollutant gases [87][88][89][90][91], are thus considered promising candidates for packing SO<sub>x</sub> and NO<sub>x</sub> adsorption columns. In this regard, the most interesting results are summarized in Table 2.

**Table 2.** MOFs potentially suitable for SO<sub>x</sub> and NO<sub>x</sub> adsorption.[92][93][94]

MOF type	Adsorbate	Adsorption capacity, <sup>1</sup> mol/kg (reported working conditions, <i>T</i> and <i>p</i> ) <sup>2</sup>	Reference
----------	-----------	---	-----------

Cu-BTC	SO <sub>2</sub>	0.71 (breakthrough, SO <sub>2</sub> /O <sub>2</sub> /He mixture, [SO <sub>2</sub> ] = 50 ppm, 773 K)	[92]
Ba – doped Cu-BTC	SO <sub>2</sub>	2.71 (breakthrough, SO <sub>2</sub> /O <sub>2</sub> /He mixture, [SO <sub>2</sub> ] = 50 ppm, 773 K)	
MOF-177	SO <sub>2</sub>	25.70 (293 K, 100 kPa)	[93]
UiO-66	NO <sub>2</sub>	1.59 (breakthrough, NO <sub>2</sub> /N <sub>2</sub> /air mixture, [NO <sub>2</sub> ] = 1000 ppm, 298 K)	[94]

<sup>1</sup> Where not explicitly reported in the cited papers, adsorption capacity values were extracted from plots using reverse engineering software. <sup>2</sup> Where not explicitly reported, working conditions imply the collection of single-component adsorption isotherms.

### 3.2. Adsorption of volatile organic compounds

Volatile organic compounds (VOCs) are a major group of air pollutants, potentially leading to photochemical smog, carcinogenesis, teratogenesis, and mutagenesis, which endanger both ecological environment and human health [95][96]. Anthropogenic VOC emissions emerge from a wide range of industrial processes, including crude oil and natural gas exploration, petroleum refining and basic chemical raw materials manufacturing [97]. Despite the immense amount of research reported regarding MOF adsorbents, literature about the adsorption of VOCs on MOFs is relatively scarce. The results regarding MOFs produced on industrial scale and commercially available are mostly summarized in Table 3.

**Table 3.** MOFs potentially suitable for adsorption of VOCs [98][99][100][101][102]

MOF type	Adsorbate	Adsorption capacity, <sup>1</sup> mol/kg (reported working conditions, <i>T</i> and <i>p</i> ) <sup>2</sup>	Reference
MOF-177	acetone	8.30 (298 K, 10.83 kPa)	[98]
	benzene	8.82 (298 K, 4.88 kPa)	
	toluene	3.77 (298 K, 1.44 kPa)	
	ethylbenzene	2.13 (298 K, 0.39 kPa)	
	m-xylene	1.92 (298 K, 0.33 kPa)	
	o-xylene	1.97 (298 K, 0.34 kPa)	
	p-xylene	1.78 (298 K, 0.32 kPa)	
	ethenylbenzene	1.61 (298 K, 0.23 kPa)	
Al-fumarate	dichloromethane	3.40 (298 K, 44.70 kPa)	[101]
	trichloromethane	2.51 (298 K, 21.44 kPa)	

UiO-66	toluene	1.64 (breakthrough, toluene/O <sub>2</sub> /argon mixture, [toluene] = 1000 ppm, 298 K)	[102]
--------	---------	---	-------

<sup>1</sup> Where not explicitly reported in the cited papers, adsorption capacity values were extracted from plots using reverse engineering software.

<sup>2</sup> Where not explicitly reported, working conditions imply the collection of single-component adsorption isotherms.

### 3.3. Adsorption of fluorinated gases

Historically, another class of gas emissions that are considered extremely harmful for the atmosphere is that including fluorinated compounds. In particular, chlorofluorocarbons (CFCs) constitute a serious threat to the stratospheric ozone layer. During the last decades, the progressive substitution of CFCs with other types of service fluids in refrigeration processes allowed to significantly recover the functionality of the planetary natural UV shield. Anyway, there are other categories of fluorinated gases that should be considered highly dangerous for Earth's atmosphere. Among them, halogenated general anesthesia gases (HGAGs) represent an emerging threat due to their worldwide growing uncontrolled discharge <sup>[103]</sup>. Indeed, Cl-containing HGAGs (e.g., enflurane and isoflurane) are also classified as CFCs, while sevoflurane, desflurane and (again) isoflurane are characterized by a global warming potential (GWP) that is three orders of magnitude higher than that of CO<sub>2</sub> <sup>[104]</sup>. Among the convenient technologies for handling emissions of HGAGs, adsorption-based ones are recognized as the most effective <sup>[105]</sup>. Indeed, non-metabolized anesthetic vapors can be captured in canisters that act as adsorption mini-columns on the vent line of the breathing system connected to the patient. Currently, studies about the potential use of MOFs for packing such canisters are quite rare. To the best of our knowledge, the only paper that deals with this topic and that envisages the use of an already commercially available adsorbent reported the sevoflurane (SF) adsorption properties of MOF-177 <sup>[106]</sup>. Despite the impressive SF adsorption capacity and affinity showed by this material, its actual implementation as anesthetic scavenger is strongly undermined due to the presence of moisture in the vent line of breathing systems.

In truth, the only MOF that proved to be practically suitable for HGAG capture is the chromium variant of MIL-101, which is not currently available in large quantities as a commercial product. Indeed, MIL-101 showed a significantly higher SF equilibrium adsorption capacity when compared to a reference adsorbent conventionally used for HGAG scavenging <sup>[107]</sup>. Moreover, when shaped and column-packed, MIL-101 revealed a much higher SF/H<sub>2</sub>O selectivity with respect to the aforementioned reference adsorbent, which suffered of “roll-up” effects when the test column reached saturation <sup>[108]</sup>. Under the same dynamic conditions (which obviously include a significant presence of moisture in the feed), the same MOF also showed a much higher performance stability when compared with the reference adsorbent after several adsorption / desorption cycles <sup>[109]</sup>. Unfortunately, as already outlined, such technologically-relevant results are not destined to improve the performances of the HGAG scavenging systems used in operating rooms (at least for the moment) due to the impossibility of large-scale MIL-101 supplies.

## 4. Conclusions

Regarding adsorption-based technologies for atmospheric emission control, there is a strong evidence of how MOFs are still far away from passing their “graduation exam”. The wide gap between laboratory results and industrial implementation is due to different factors. First, even when a MOF that performs well in a specific process (e.g., CO<sub>2</sub> adsorption) is commercially available in large quantities, economic observations still make designers tend towards more traditional adsorbents (e.g., zeolites, activated carbons). Indeed, the cost per mass unit of commercial MOFs basically is orders of magnitude higher than that of other materials, whose industrial use is already well-established. Moreover, there are cases (like adsorption processes for HGAG scavenging) in which a specific MOF remarkably outperforms currently employed adsorbents, but it is not industrially produced, thus strongly limiting its possibilities of large-scale use. To overcome such limitations, it is to be hoped that chemical industry will be able to provide more and more mass-produced MOFs at increasingly competitive costs in the future.

## References

1. IPCC, 2014: Climate Change 2014: Synthesis Report. Contribution of Working Groups I, II and III to the Fifth Assessment Report of the Intergovernmental Panel on Climate Change [Core Writing Team, R.K. Pachauri and L.A. Meyer (eds.)]. IPCC, Geneva, Switzerland, 151 pp.

2. Wan, X.; Zhang, Z. Climate warming and humans played different roles in triggering Late Quaternary extinctions in east and west Eurasia. *R. Soc. B* 2017, 284, 20162438.
3. Mersmann, A.; Fill, B.; Hartmann R.; Maurer S. The Potential of Energy Saving by Gas-Phase Adsorption Processes. *Eng. Technol.* 2000, 23, 937-944.
4. Broom, D.P.; Thomas, M. Gas adsorption by nanoporous materials: Future applications and experimental challenges. *MRS Bull.* 2013, 38, 412-421.
5. Li, J.-R.; Kuppler, R.J.; Zhou, H.-C. Selective gas adsorption and separation in metal–organic frameworks. *Soc. Rev.* 2009, 38, 1477-1504.
6. Raynaud, D.; Barnol, J.M. An Antarctic ice core reveals atmospheric CO<sub>2</sub> variations over the past few centuries. *Nature* 1985, 315, 309-311.
7. Climate Change: Atmospheric Carbon Dioxide. Available online: <https://www.climate.gov/news-features/understanding-climate/climate-change-atmospheric-carbon-dioxide> (accessed on 8th January 2020).
8. Schneider, S. The Greenhouse Effect: Science and Policy. *Science* 1989, 243, 771-781.
9. Jiang, L.; Gonzalez-Diaz, A.; Ling-Chin, J.; Roskilly, A.P.; Smallbone, A.J. Post-combustion CO<sub>2</sub> capture from a natural gas combined cycle power plant using activated carbon adsorption. *Energy* 2019, 245, 1-15.
10. Oreggioni, G.D.; Brandani, S.; Luberti, M.; Baykan, Y.; Friedrich, D.; Ahn, H. CO<sub>2</sub> capture from syngas by an adsorption process at a biomass gasification CHP plant: its comparison with amine-based CO<sub>2</sub> Int. *J. Greenhouse Gas Control* 2015, 35, 71-81.
11. Gargiulo, N.; Shibata, K.; Peluso, A.; Aprea, P.; Valente, T.; Pezzotti, G.; Shiono, T.; Caputo, D. Reinventing rice husk ash: derived NaX zeolite as a high-performing CO<sub>2</sub> Int. *J. Environ. Sci. Technol.* 2018, 15, 1543-1550.
12. Gargiulo, N.; Pepe, F.; Caputo, D. CO<sub>2</sub> adsorption by functionalized nanoporous materials: a review. *Nanosci. Nanotechnol.* 2014, 14, 1811-1822.
13. Gargiulo, N.; Pepe, F.; Caputo, D. Modeling carbon dioxide adsorption on polyethylenimine-functionalized TUD-1 mesoporous silica. *Colloid Interface Sci.* 2012, 367, 348-354.
14. Gargiulo, N.; Peluso, A.; Aprea, P.; Pepe, F.; Caputo, D. CO<sub>2</sub> Adsorption on polyethylenimine-functionalized SBA-15 mesoporous silica: isotherms and modeling. *Chem. Eng. Data* 2014, 59, 896-902.
15. Gargiulo, N.; Macario, A.; Iucolano, F.; Giordano, G.; Caputo, D. Modeling the adsorption of CO<sub>2</sub>/N<sub>2</sub> mixtures on siliceous nanoporous materials. *Adv. Mater.* 2015, 7, 258-263.
16. Gargiulo, N.; Verlotta, A.; Peluso, A.; Aprea, P.; Caputo, D. Modeling the performances of a CO<sub>2</sub> adsorbent based on polyethylenimine-functionalized macro-/mesoporous silica monoliths. *Microporous Mesoporous Mater.* 2015, 215, 1-7.
17. Ghanbari, T.; Abnisa, F.; Wan Daud, W.M.A. A review on production of metal organic frameworks (MOF) for CO<sub>2</sub> Sci. *Total Environ.* 2020, 707, 135090.
18. Saqib, S.; Rafiq, S.; Chawla, M.; Saeed, M.; Muhammad, N.; Khurram, S.; Majeed, K.; Khan, A.L.; Ghauri, M.; Jamil, F.; Aslam, M. Facile CO<sub>2</sub> separation in composite membranes. *Eng. Technol.* 2019, 42, 30-44.
19. Saha, D.; Bao, Z.; Jia, F.; Deng, S. Adsorption of CO<sub>2</sub>, CH<sub>4</sub>, N<sub>2</sub>O, and N<sub>2</sub> on MOF-5, MOF-177, and Zeolite 5A. *Sci. Technol.* 2010, 44, 1820-1826.
20. Tsivadze, A.Y.; Aksyutin, O.E.; Ishkov, A.G.; Knyazeva, M.K.; Solovtsova, O.V.; Men'shchikov, I.E.; Fomkin, A.A.; Shkolnik, A.V.; Khozina, E.V.; Grachev, V.A. Metal-organic framework structures: adsorbents for natural gas storage. *Chem. Rev.* 2019, 88, 925-978.
21. Sircar, S. Pressure Swing Adsorption. *Eng. Chem. Res.* 2002, 41, 1389-1392.
22. Chou, C.-T.; Chen, C.-Y. Carbon dioxide recovery by vacuum swing adsorption. *Purif. Technol.* 2004, 39, 51-65.
23. Ullah, S.; Bustam, M.A.; Assiri, M.A.; Al-Sehemi, A.G.; Sagir, M.; Abdul Kareem, F.A.; Elkhalfah, A.E.I.; Mukhtar, A.; Gonnafa, G. Synthesis, and characterization of metal-organic frameworks -177 for static and dynamic adsorption behavior of CO<sub>2</sub> and CH<sub>4</sub>. *Microporous Mesoporous Mater.* 2019, 288, 109569.
24. Mohamedali, M.; Henni, A.; Ibrahim, H. Investigation of CO<sub>2</sub> capture using acetate-based ionic liquids incorporated into exceptionally porous metal–organic frameworks. *Adsorption* 2019, 25, 675-692.
25. Tranchemontagne, D.J.; Hunt, J.R.; Yaghi, O.M. Room temperature synthesis of metal-organic frameworks: MOF-5, MOF-74, MOF-177, MOF-199, and IRMOF-0. *Tetrahedron* 2008, 64, 8553-8557.
26. Aprea, P.; Caputo, D.; Gargiulo, N.; Iucolano, F.; Pepe, F. Modeling Carbon Dioxide Adsorption on Microporous Substrates: Comparison between Cu-BTC Metal-Organic Framework and 13X Zeolitic Molecular Sieve. *Chem. Eng. Data* 2010, 55, 3655-3661.



27. Musto, P.; La Manna, P.; Pannico, M.; Mensitieri, G.; Gargiulo, N.; Caputo, D. Molecular interactions of CO<sub>2</sub> with the Cu BTC metal organic framework: An FTIR study based on two-dimensional correlation spectroscopy. *Mol. Struct.* 2018, 1 166, 326-333.
28. Hamon, L.; Jolimaître, E.; Pirngruber, G.D. CO<sub>2</sub> and CH<sub>4</sub> Separation by Adsorption Using Cu-BTC Metal-Organic Framework. *Eng. Chem. Res.* 2010, 49, 7497-7503.
29. Ye, S.; Jiang, X.; Ruan, L.-W.; Liu, B.; Wang, Y.-M.; Zhu, J.-F.; Qiu, L.-G. Post-combustion CO<sub>2</sub> capture with the HKUST-1 and MIL-101(Cr) metal-organic frameworks: Adsorption, separation and regeneration investigations. *Microporous Mesoporous Mater.* 2013, 179, 191-197.
30. Kloutse, F.A.; Hourri, A.; Natarajan, S.; Benard, P.; Chahine, R. Systematic study of the excess and the absolute adsorption of N<sub>2</sub>/H<sub>2</sub> and CO<sub>2</sub>/H<sub>2</sub> mixtures on Cu-BTC. *Adsorption* 2019, 25, 941-950.
31. Da Silva, F.; Magalhães, G.; Jardim, E.; Silvestre-Albero, J.; Sepúlveda-Escribano, A.; De Azevedo, D.; De Lucena, S. CO<sub>2</sub> adsorption on ionic liquid-modified Cu-BTC: Experimental and simulation study. *Sci. Technol.* 2015, 33, 223-242.
32. Mohamedali, M.; Henni, A.; Ibrahim, H. Markedly improved CO<sub>2</sub> uptake using imidazolium-based ionic liquids confined into HKUST-1 frameworks. *Microporous Mesoporous Mater.* 2019, 284, 98-110.
33. Zhou, L.; Niu, Z.; Jin, X.; Tang, L.; Zhu, L. Effect of Lithium Doping on the Structures and CO<sub>2</sub> Adsorption Properties of Metal-Organic Frameworks HKUST-1. *ChemistrySelect* 2018, 3, 12865-12870.
34. Prestipino, C.; Regli, L.; Vitillo, J.G.; Bonino, F.; Damin, A.; Lamberti, C.; Zecchina, A.; Solari, P.L.; Kongshaug, K.O.; Bordiga, S. Local Structure of Framework Cu(II) in HKUST-1 Metallorganic Framework: Spectroscopic Characterization upon Activation and Interaction with Adsorbates. *Mater.* 2006, 18, 1337-1346.
35. Low, J.J.; Benin, A.I.; Jakubczak, P.; Abrahamian, J.F.; Faheem, S.A.; Willis, R.R. Virtual High Throughput Screening Confirmed Experimentally: Porous Coordination Polymer Hydration. *Am. Chem. Soc.* 2009, 131, 15834-15842.
36. Al-Janabi, N.; Hill, P.; Torrente-Murciano, L.; Garforth, A.; Gorgojo, P.; Siperstein, F.; Fan, X. Mapping the Cu-BTC metal-organic framework (HKUST-1) stability envelope in the presence of water vapour for CO<sub>2</sub> adsorption from flue gases. *Eng. J.* 2015, 281, 669-677.
37. Bao, Z.; Yu, L.; Ren, Q.; Lu, X.; Deng, S. Adsorption of CO<sub>2</sub> and CH<sub>4</sub> on a magnesium-based metal organic framework. *Colloid Interface Sci.* 2011, 353, 549-556.
38. Grajciar, L.; Nachtigall, P.; Bludsky, O.; Rubes, M. Accurate Ab Initio Description of Adsorption on Coordinatively Unsaturated Cu<sup>2+</sup> and Fe<sup>3+</sup> Sites in MOFs. *Chem. Theor. Comput.* 2015, 11, 230-238.
39. Mason, J.A.; Sumida, K.; Herm, Z.R.; Krishna, R.; Long, J.R. Evaluating metal-organic frameworks for post-combustion carbon dioxide capture via temperature swing adsorption. *Energy Environ. Sci.* 2011, 4, 3030-3040.
40. Herm, Z.R.; Krishna, R.; Long, J.R. CO<sub>2</sub>/CH<sub>4</sub>, CH<sub>4</sub>/H<sub>2</sub> and CO<sub>2</sub>/CH<sub>4</sub>/H<sub>2</sub> separations at high pressures using Mg<sub>2</sub>(dobdc). *Microporous Mesoporous Mater.* 2012, 151, 481-487.
41. Remy, T.; Peter, S.A.; Van Der Perre, S.; Valvekens, P.; De Vos, D.E.; Baron, G.V.; Denayer, J.F.M. Selective Dynamic CO<sub>2</sub> Separations on Mg-MOF-74 at Low Pressures: A Detailed Comparison with 13X. *Phys. Chem. C* 2013, 117, 9301-9310.
42. Qasem, N.A.A.; Ben-Mansour, R. Adsorption breakthrough and cycling stability of carbon dioxide separation from CO<sub>2</sub>/N<sub>2</sub>/H<sub>2</sub>O mixture under ambient conditions using 13X and Mg-MOF-74. *Energy* 2018, 230, 1093-1107.
43. Mangano, E.; Kahr, J.; Wright, P.A.; Brandani, S. Accelerated degradation of MOFs under flue gas conditions. *Faraday Discuss.* 2016, 192, 181-195.
44. Moon, H.-S.; Moon, J.-H.; Chun, D.H.; Park, Y.C.; Yun, Y.N.; Sohail, M.; Baek, K.; Kim, H. Synthesis of [Mg<sub>2</sub>(DOBDC)(DMF)<sub>2</sub>]/polystyrene composite and its carbon dioxide adsorption. *Microporous Mesoporous Mater.* 2016, 232, 161-166.
45. Cao, Y.; Song, F.; Zhao, Y.; Zhong, Q. Capture of carbon dioxide from flue gas on TEPA-grafted metal-organic framework Mg<sub>2</sub>(dobdc). *Environ. Sci.* 2013, 25, 2081-2087.
46. Su, X.; Bromberg, L.; Martis, V.; Simeon, F.; Huq, A.; Hatton, T.A. Postsynthetic Functionalization of Mg-MOF-74 with Tetraethylenepentamine: Structural Characterization and Enhanced CO<sub>2</sub> ACS Appl. Mater. Interfaces 2017, 9, 11299-11306.
47. Bernini, M.C.; García Blanco, A.A.; Villarroel-Rocha, J.; Fairen-Jimenez, D.; Sapag, K.; Ramirez-Pastor, A.J.; Narda, G. E. Tuning the target composition of amine-grafted CPO-27-Mg for capture of CO<sub>2</sub> under post-combustion and air filtering conditions: a combined experimental and computational study. *Dalton Trans.* 2015, 44, 18970-18982.
48. Pérez-Pellitero, J.; Amrouche, H.; Siperstein, F.R.; Pirngruber, G.; Nieto-Draghi, C.; Chaplais, G.; Simon-Masseron, A.; Bazer-Bachi, D.; Peralta, D.; Bats, N. Adsorption of CO<sub>2</sub>, CH<sub>4</sub>, and N<sub>2</sub> on zeolitic imidazolate frameworks: Experiment

s and simulations. *Eur. J.* 2010, 16, 1560-1571.

49. McEwen, J.; Hayman, J.-D.; Ozgur Yazaydin, A. A comparative study of CO<sub>2</sub>, CH<sub>4</sub> and N<sub>2</sub> adsorption in ZIF-8, Zeolite-13X and BPL activated carbon. *Phys.* 2013, 412, 72-76.
50. Danaci, D.; Singh, R.; Xiao, P.; Webley, P.A. Assessment of ZIF materials for CO<sub>2</sub> capture from high pressure natural gas streams. *Eng. J.* 2015, 280, 486-493.
51. Zhang, Z.; Xian, S.; Xi, H.; Wang, H.; Li, Z. Improvement of CO<sub>2</sub> adsorption on ZIF-8 crystals modified by enhancing basicity of surface. *Eng. Sci.* 2011, 66, 4878-4888.
52. Zhang, Z.; Xian, S.; Xia, Q.; Wang, H.; Li, Z.; Li, J. Enhancement of CO<sub>2</sub> Adsorption and CO<sub>2</sub>/N<sub>2</sub> Selectivity on ZIF-8 via a Postsynthetic Modification. *AIChE J.* 2013, 59, 2195-2206.
53. Martínez, F.; Sanz, R.; Orcajo, G.; Briones, D.; Yáñez, V. Amino-impregnated MOF materials for CO<sub>2</sub> capture at post-combustion conditions. *Eng. Sci.* 2016, 142, 55-61.
54. Sayari, A.; Belmabkhout, Y. Stabilization of Amine-Containing CO<sub>2</sub> Adsorbents: Dramatic Effect of Water Vapor. *Am. Chem. Soc.* 2010, 132, 6312-6314.
55. Cho, K.Y.; An, H.; Do, X.H.; Choi, K.; Yoon, H.G.; Jeong, H.-K.; Lee, J.S.; Baek, K.-Y. Synthesis of amine-functionalized ZIF-8 with 3-amino-1,2,4-triazole by postsynthetic modification for efficient CO<sub>2</sub>-selective adsorbents and beyond. *Mater. Chem. A* 2018, 6, 18912-18919.
56. Tsai, C.-W.; Niemantsverdriet, J.W.; Langner, E.H.G. Enhanced CO<sub>2</sub> adsorption in nano-ZIF-8 modified by solvent assisted ligand exchange. *Microporous Mesoporous Mater.*, 2018, 262, 98-105.
57. Gadipelli, S.; Travis, W.; Zhou, W.; Guo, Z. A thermally derived and optimized structure from ZIF-8 with giant enhancement in CO<sub>2</sub> Energy Environ. Sci. 2014, 7, 2232-2238.
58. Ghahramaninezhad, M.; Soleimani, B.; Niknam Shahrak, M. A simple and novel protocol for Li-trapping with a POM/MOF nano-composite as a new adsorbent for CO<sub>2</sub> New J. Chem. 2018, 42, 4639-4645.
59. Mohamedali, M.; Ibrahim, H.; Henni, A. Incorporation of acetate-based ionic liquids into a zeolitic imidazolate framework (ZIF-8) as efficient sorbents for carbon dioxide capture. *Eng. J.* 2018, 334, 817-828.
60. Zeeshan, M.; Keskin, S.; Uzun, A. Enhancing CO<sub>2</sub>/CH<sub>4</sub> and CO<sub>2</sub>/N<sub>2</sub> separation performances of ZIF-8 by postsynthetic modification with [BMIM][SCN]. *Polyhedron* 2018, 155, 485-492.
61. Ferreira, T.J.; Ribeiro, R.P.P.L.; Mota, J.P.B.; Rebelo, L.P.N.; Esperança, J.M.S.S.; Esteves, I.A.A.C. Ionic liquid-impregnated metal-organic frameworks for CO<sub>2</sub>/CH<sub>4</sub> ACS Appl. Nano Mater. 2019, 2, 7933-7950.
62. Idris, I.; Abdullah, A.; Shamsudin, I.K.; Othman, M.R. Comparative analyses of carbon dioxide capture from power plant flue gas surrogate by micro and mesoporous adsorbents. *Environ. Chem. Eng.* 2019, 7, 103115.
63. Wongsakulphasatch, S.; Kiatkittipong, W.; Saupsor, J.; Chaiwisesphol, J.; Piroonlerkgul, P.; Parasuk, V.; Assabumrung, S. Effect of Fe open metal site in metal-organic frameworks on post-combustion CO<sub>2</sub> capture performance. *Greenhouse Gases Sci. Technol.* 2017, 7, 383-394.
64. Chen, Y.; Qiao, Z.; Huang, J.; Wu, H.; Xiao, J.; Xia, Q.; Xi, H.; Hu, J.; Zhou, J.; Li, Z. Unusual moisture-enhanced CO<sub>2</sub> capture within microporous PCN-250 frameworks. *ACS Appl. Mater. Interfaces* 2020, 10, 38638-38647.
65. Yang, Q.; Wiersum, A.D.; Jobic, H.; Guillerm, V.; Serre, C.; Llewellyn, P.L.; Maurin, G. Understanding the thermodynamic and kinetic behavior of the CO<sub>2</sub>/CH<sub>4</sub> gas mixture within the porous zirconium terephthalate UiO-66(Zr): A joint experimental and modeling approach. *Phys. Chem. C* 2011, 115, 13768-13774.
66. Cavka, J.H.; Grande, C.A.; Mondino, G.; Blom, R. High pressure adsorption of CO<sub>2</sub> and CH<sub>4</sub> on Zr-MOFs. *Eng. Chem. Res.* 2014, 53, 15500-15507.
67. Andersen, A.; Divekar, S.; Dasgupta, S.; Cavka, J.H.; Aarti, A.; Nanoti, A.; Spjelkavik, A.; Goswami, A.N.; Garg, M.O.; Blom, R. On the development of Vacuum Swing adsorption (VSA) technology for post-combustion CO<sub>2</sub> Energy Procedia 2013, 37, 33-39.
68. Kim, S.-N.; Lee, Y.-R.; Hong, S.-H.; Jang, M.-S.; Ahn, W.-S. Pilot-scale synthesis of a zirconium-benzenedicarboxylate UiO-66 for CO<sub>2</sub> adsorption and catalysis. *Today* 2015, 245, 54-60.
69. Hu, Z.; Sun, Y.; Zeng, K.; Zhao, D. Structural-failure resistance of metal-organic frameworks toward multiple-cycle CO<sub>2</sub> Chem. Commun. 2017, 53, 8653-8656.
70. Edubilli, S.; Gumma, S. A systematic evaluation of UiO-66 metal organic framework for CO<sub>2</sub>/N<sub>2</sub> Sep. Purif. Technol. 2019, 224, 85-94.
71. Abdullah, A.; Idris, I.; Shamsudin, I.K.; Othman, M.R. Methane enrichment from high carbon dioxide content natural gas by pressure swing adsorption. *Nat. Gas Sci. Eng.* 2019, 69, 102929.

72. Hon Lau, C.; Babarao, R.; Hill, M.R. A route to drastic increase of CO<sub>2</sub> uptake in Zr metal organic framework UiO-66. *Commun.* 2013, 49, 3634-3636.
73. Hong, D.H.; Suh, M.P. Enhancing CO<sub>2</sub> separation ability of a metal-organic framework by post-synthetic ligand exchange with flexible aliphatic carboxylates. *Eur. J.* 2014, 20, 426-434.
74. Li, L.J.; Liao, P.Q.; He, C.T.; Wei, Y.S.; Zhou, H.L.; Lin, J.M.; Li, X.Y.; Zhang, J.P. Grafting alkylamine in UiO-66 by charge-assisted coordination bonds for carbon dioxide capture from high-humidity flue gas. *Mater. Chem. A* 2015, 3, 21849-21855.
75. Xian, S.; Wu, Y.; Wu, J.; Wang, X.; Xiao, J. Enhanced dynamic CO<sub>2</sub> adsorption capacity and CO<sub>2</sub>/CH<sub>4</sub> selectivity on polyethylenimine-impregnated UiO-66. *Eng. Chem. Res.* 2015, 54, 11151-11158.
76. Mutyala, S.; Yu, Y.-D.; Jin, W.-G.; Wang, Z.-S.; Zheng, D.-Y.; Ye, C.-R.; Luo, B. CO<sub>2</sub> capture using amine incorporated UiO-66 in atmospheric pressure. *Porous Mater.* 2019, 26, 1831-1838.
77. Niu, Z.; Guan, Q.; Shi, Y.; Chen, Y.; Chen, Q.; Kong, Z.; Ning, P.; Tian, S.; Miao, R. A lithium-modified zirconium-based metal organic framework (UiO-66) for efficient CO<sub>2</sub> New J. Chem. 2018, 42, 19764-19770.
78. MOF Manufacturing. Available online: <https://www.moftechnologies.com/manufacturing/> (accessed on 5th March 2020).
79. Chanut, N.; Wiersum, A.D.; Lee, U.-H.; Hwang, Y.K.; Ragon, F.; Chevreau, H.; Bourrelly, S.; Kuchta, B.; Chang, J.-S.; Serre, C.; Llewellyn, P.L. Observing the effects of shaping on gas adsorption in metal-organic frameworks. *J. Inorg. Chem.* 2016, 2016, 4416-4423.
80. Zheng, J.; Cui, X.; Yang, Q.; Ren, Q.; Yang, Y.; Xing, H. Shaping of ultrahigh-loading MOF pellet with a strongly anti-tearing binder for gas separation and storage. *Eng. J.* 2018, 354, 1075-1082.
81. Mallick, A.; Mouchaham, G.; Bhatt, P.M.; Liang, W.; Belmabkhout, Y.; Adil, K.; Jamal, A.; Eddaoudi, M. Advances in Shaping of Metal-Organic Frameworks for CO<sub>2</sub> Capture: Understanding the Effect of Rubbery and Glassy Polymeric Binders. *Eng. Chem. Res.* 2018, 57, 16897-16902.
82. Ribeiro, R.P.P.L.; Antunes, C.L.; Garate, A.U.; Portela, A.F.; Plaza, M.G.; Mota, J.P.B.; Esteves, I.A.A.C. Binderless shaped metal-organic framework particles: Impact on carbon dioxide adsorption. *Microporous Mesoporous Mater.* 2019, 275, 111-121.
83. Valizadeh, B.; Nguyen, T.N.; Stylianou, K.C. Shape engineering of metal-organic frameworks. *Polyhedron* 2018, 145, 1-15.
84. Danaci, D.; Bui, M.; Mac Dowell, N.; Petit, C. Exploring the limits of adsorption-based CO<sub>2</sub> capture using MOFs with P VSA – from molecular design to process economics. *Syst. Des. Eng.* 2020, 5, 212-231.
85. World Energy Outlook 2016 – Analysis – IEA. Available online: <https://www.iea.org/reports/world-energy-outlook-2016> (accessed on 26th March 2020).
86. Fioletov, V.E.; McLinden, C.A.; Krotkov, N.; Li, C.; Joiner, J.; Theys, N.; Carn, S.; Moran, M.D. A global catalogue of large SO<sub>2</sub> sources and emissions derived from the Ozone Monitoring Instrument. *Chem. Phys.* 2016, 16, 11497-11519.
87. Britt, D.; Tranchemontagne, D.; Yaghi, O.M. Metal-organic frameworks with high capacity and selectivity for harmful gases. *Natl. Acad. Sci. U.S.A.* 2008, 105, 11623-11627.
88. Bobbitt, N.S.; Mendonca, M.L.; Howarth, A.J.; Islamoglu, T.; Hupp, J.T.; Farha, O.K.; Snurr, R.Q. Metal-organic frameworks for the removal of toxic industrial chemicals and chemical warfare agents. *Soc. Rev.* 2017, 46, 3357-3385.
89. Wang, H.; Lustig, W.P.; Li, J. Sensing and capture of toxic and hazardous gases and vapors by metal-organic frameworks. *Soc. Rev.* 2018, 47, 4729-4756.
90. Han, X.; Yang, S.; Schröder, M. Porous metal-organic frameworks as emerging sorbents for clean air. *Rev. Chem.* 2019, 3, 108-118.
91. Glomb, S.; Woschko, D.; Makhoulfi, G.; Janiak, C. Metal-organic frameworks with internal urea-functionalized dicarboxylate linkers for SO<sub>2</sub> and NH<sub>3</sub> ACS Appl. Mater. Interfaces 2017, 9, 37419-37434.
92. Dathe, H.; Peringer, E.; Roberts, V.; Jentys, A.; Lercher, J.A. Metal organic frameworks based on Cu<sup>2+</sup> and benzene-1,3,5-tricarboxylate as host for SO<sub>2</sub> trapping agents. *Comptes Rendus Chim.* 2005, 8, 753-763.
93. Brandt, P.; Nuhnen, A.; Lange, M.; Möllmer, J.; Weingart, O.; Janiak, C. Metal-organic frameworks with potential application for SO<sub>2</sub> separation and flue gas desulfurization. *ACS Appl. Mater. Interfaces* 2019, 11, 17350-17358.
94. Ebrahim, A.M.; Levasseur, B.; Badosz T.J., Interactions of NO<sub>2</sub> with Zr-based MOF: Effects of the size of organic linkers on NO<sub>2</sub> adsorption at ambient conditions. *Langmuir* 2013, 29, 168-174.
95. Tancrede, M.; Wilson, R.; Zeise, L.; Crouch, E.A.C. The carcinogenic risk of some organic vapors indoors: A theoretical survey. *Environ.* 1987, 19, 2187-2205.

96. Molhave, L. Indoor climate, air pollution, and human comfort. *Expo. Sci. Environ. Epidemiol.* 1991, 1, 63-81.
97. Zheng, C.; Shen, J.; Zhang, Y.; Huang, W.; Zhu, X.; Wu, X.; Chen, L.; Gao, X.; Cen, K. Quantitative assessment of industrial VOC emissions in China: Historical trend, spatial distribution, uncertainties, and projection. *Environ.* 2017, 150, 116-125.
98. Yang, K.; Xue, F.; Sun, Q.; Yue, R.; Lin, D. Adsorption of volatile organic compounds by metal-organic frameworks MOF-177. *Environ. Chem. Eng.* 2013, 1, 713-718.
99. Saha, D.; Deng, S. Structural Stability of Metal Organic Framework MOF-177. *Phys. Chem. Lett.* 2010, 1, 73-78.
100. Vellingiri, K.; Szulejko, J.E.; Kumar, P.; Kwon, E.E.; Kim, K-H.; Deep, A.; Boukhvalov, D.W.; Brown, R.J.C. Metal organic frameworks as sorption media for volatile and semi-volatile organic compounds at ambient conditions. *Rep.* 2016, 6, 27813.
101. Zhou, L.; Zhang, X.; Chen, Y. Facile synthesis of Al-fumarate metal-organic framework nano-flakes and their highly selective adsorption of volatile organic compounds. *Lett.* 2017, 197, 224-227.
102. Zhang, X.; Yang, Y.; Song, L.; Chen, J.; Yang, Y.; Wang Y. Enhanced adsorption performance of gaseous toluene on defective UiO-66 metal organic framework: Equilibrium and kinetic studies. *Hazard. Mater.* 2019, 365, 597-605.
103. Uzoigwe, C.E.; Sanchez Franco, L.C.; Forrest, M.D. Iatrogenic greenhouse gases: the role of anaesthetic agents. *J. Hosp. Med.* 2016, 77, 19-23.
104. Ishizawa, Y. General anesthetic gases and the global environment. *Analg.* 2011, 112 213-217.
105. Anesthetic Gases: Guidelines for Workplace Exposures | Occupational Safety and Health Administration. Available online: <https://www.osha.gov/dts/osta/anestheticgases/> (accessed on 1st April 2020).
106. Gargiulo, N.; Peluso, A.; Aprea, P.; Eić, M.; Caputo, D. An insight into clustering of halogenated anesthetics molecules in metal-organic frameworks: Evidence of adsorbate self-association in micropores. *Colloid Interface Sci.* 2019, 554, 463-467.
107. Gargiulo, N.; Peluso, A.; Aprea, P.; Hua, Y.; Filipović, D.; Caputo, D.; Eić, M. A chromium-based metal organic framework as a potential high performance adsorbent for anaesthetic vapours. *RSC Adv.* 2014, 4, 49478-49484.
108. Hua, Y.; Gargiulo, N.; Peluso, A.; Aprea, P.; Eić, M.; Caputo, D. Adsorption Behavior of Halogenated Anesthetic and Water Vapor on Cr-Based MOF (MIL-101) Adsorbent. Part I. Equilibrium and Breakthrough Characterizations. *Ing. Tech.* 2016, 88, 1730-1738.
109. Hua, Y.; Gargiulo, N.; Peluso, A.; Aprea, P.; Eić, M.; Caputo, D. Adsorption Behavior of Halogenated Anesthetic and Water Vapor on Cr-Based MOF (MIL-101) Adsorbent. Part II. Multiple-Cycle Breakthrough Tests. *Ing. Tech.* 2016, 88, 1739-1745.

---

Retrieved from <https://encyclopedia.pub/entry/history/show/4118>